

POST WELD HEAT TREATMENT FOR RESIDUAL STRESSES RELIEVING IN WELDED STEEL PLATES: MODELING AND EXPERIMENTAL ANALYSIS

Telmo Viana Rodrigues, telmoviana@gmail.com

Jorge Carlos Ferreira Jorge, jorgecfjorge@gmail.com

Luís Felipe Guimarães de Souza, lfelipe@cefet-rj.br

Pedro Manuel Calas Lopes Pacheco, calas@cefet-rj.br

CEFET/RJ - PPEMM - Programa de Pós-Graduação em Engenharia Mecânica e Tecnologia de Materiais
Av. Maracanã, 229, 20271-110 - Rio de Janeiro - RJ - Brasil

Abstract. *Welding is the main method among fabrication processes available for joining mechanical elements. It is a complex process where localized intensive heat input is furnished to a piece promoting mechanical and metallurgical changes. Phenomenological aspects of welding process involve couplings among different physical processes and its description is unusually complex. Basically, three couplings are essential: thermal, phase transformation and mechanical phenomena. Among the disadvantages related to the welding processes is the generation of the residual stress due to the thermal gradient imposed to the workpiece in association to geometric restrictions. The presence of tensile residual stresses can be especially dangerous to mechanical components submitted to fatigue loadings. In the presence of tensile stresses promoted by the operational loading conditions, both stresses are added resulting in much higher tensile stress levels than the ones predicted. The present contribution regards on study post weld heat treatments (PWHT) for residual stress relieving in welded steel plates using experimental analysis and a numerical model. First experimental analysis is used to assess the temperature evolution during welding using thermocouples and an infrared camera. The obtained experimental data is used to calibrate a coupled bidimensional thermo-elastoplastic finite element model with temperature-dependent thermomechanical properties. This parametric model is used to study the effect of the PWHT on the residual stresses of welded steel plates. Results indicate that the temperature levels of the PWHT affect the values of residual stresses. The proposed methodology can be used in complex geometries as a powerful tool to study and adjust the PWHT to minimize the residual stresses on welded mechanical components.*

Keywords: *Welding, Stress-Relieving, Modeling*

1. INTRODUCTION

Welding is the most common method among the fabrication processes available for joining mechanical elements. The great variety of welding processes offers versatility whose application can vary from small electronic components to shipbuilding industry. Each welding process has its proper characteristics including advantages and disadvantages which must be carefully balanced for the specific application or project.

Phenomenological aspects of welding involve basically, three couplings: thermal, phase transformation and mechanical phenomena. Due to the complexity of these couplings interaction, several authors have addressed these three aspects separately: some authors consider only the thermomechanical coupling (Bang *et al.*, 2002; Teng and Chang, 2004; Costa *et al.*, 2007) but it is important to note that in many situations the phase transformation must be also considered (Zacharia *et al.*, 1995; Taljat *et al.*, 1998; Ronda and Oliver, 2000; Silva and Pacheco, 2005, 2007; Silva, 2007).

Among the disadvantages related to the welding processes based on the electric arc is the generation of the residual stress due to the thermal gradient imposed to the workpiece in association to geometric restrictions. It is well known that residual stress plays a preponderant part in the structural integrity of a mechanical component. Nevertheless, the presence of residual stress is not fully considered in traditional design of mechanical components. Some traditional design methodologies assume that the component is submitted to a null stress state before the application of the operational loading and the use of precise analytic and/or computational methods is not sufficient for a reliable structural integrity life prediction. The presence of tensile residual stresses can be especially dangerous to mechanical components submitted to fatigue loadings. In the presence of tensile stresses promoted by the operational loading conditions, both stresses are added resulting in much higher tensile stress levels than the ones predicted, and may be responsible for nucleation and propagation of cracks.

In order to minimize the residual stress effects in a welded joint some precautions may be carried out as the application of preheating or the post welding heat treatments (PWHT). There are many options of heat treatments which can be applied to the welded joint aiming to reduce the residual stress levels being the most common the annealing for stress relieving. The annealing for stress relieving consists on heating the workpiece uniformly in a range of temperature for specific period of time followed by air cooling to room temperature. The parameters selection (temperature and time) depends particularly on the base and weld metal chemical compositions. It is due to the possibility of occurring undesirable phase transformations, microstructural changes and carbides precipitation

mechanisms for instance which can impair the mechanical properties, particularly the notch toughness. Such phenomena can arise more complex when base metal and weld metal are not similar, so it is necessary to establish *PWHT* parameters to attend both alloys. Depending on the *PWHT* temperature and the applied technique a complete remove of residual stress can be obtained. Beyond the removal of residual stress the tensile strength and the yield strength also can be affected particularly on the heat affected zone (*HAZ*) of high strength low alloy carbon steels due to the tempering action of the *PWHT*. In other situations depending on the alloy composition local brittle zones can arise also on the *HAZ*. Form the exposed it is expected as an ideal condition the selection of the temperature for the *PWHT* that leads to the maximum reduction of the residual stress levels without impairing the mechanical properties of the welded joint by the occurrence of phase transformations or microstructural changes.

Some authors have addressed the effect of *PWHT* temperature. Cao *et al.* (2009) studied the effects of *PWHT* on metallurgical and tensile properties of Inconel 718 alloy butt joints welded by laser process. Kanga *et al.* (2007) investigated the effects of residual stress and heat treatment on fatigue strength of weldments. Paradowska *et al.* (2010) used hole drilling techniques to assess how local *PWHT* contributes for residual stress reduction and improvement in fatigue life of welded tubular joints.

Figure 1 shows residual stress reduction for different *PWHT* temperatures as a function of time for a steel containing 0.21% carbon and 1.44% manganese (Linnert, 1967). Several mechanisms contribute to residual stress relieve and the larger release occurs during the first hour. Recovery phenomenon and material yielding are the major mechanisms involved. At low temperatures recovery is the first effect to be found. Despite there is no observable changes in grain structure some decrease in residual stress can be attained, being it attributed to the reduction of the dislocations density. Similar to a creep phenomena, effective relaxation can be obtained at higher temperatures where the yield strength of the metal is lower than the residual stress imposed to metal that will flow plastically until the stress is reduced to the yield strength of the metal at the treatment temperature. The plastic deformation resulting from the flow can cause a progressive strengthening as cold working during stress relief. As a resulting effect, the higher the initial residual stress the higher the residual stress after stress relief at a given temperature. In association with the plastic deformation developed during relief other effects as recrystalization which corresponds to the formation of new strain free grains followed by grain growth can contribute for the relaxation effect. It is important to observe that the occurrence of recrystalization depends on strain hardening level in such way that a competitive mechanism between strain hardening and recrystalization can occur.

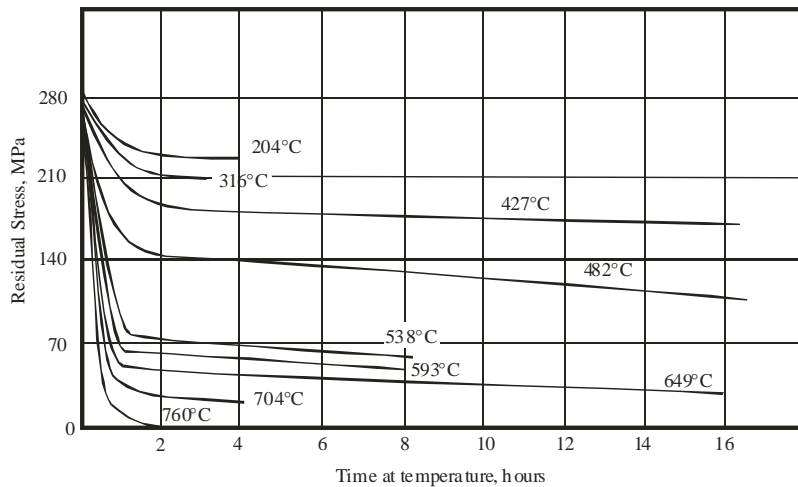


Figure 1. Residual stress relieving as a function of *PWHT* temperature (Linnert, 1967).

The present contribution regards on the study of the influence of the *PWHT* temperature on residual stresses relieve using a coupled bidimensional thermo-elastoplastic finite element model with temperature-dependent thermomechanical properties. The finite element analysis is carried out in three stages: 1) *welding process*; 2) *cooling process* and 3) *post weld heat treatment (PWHT)*. Its worthy of note that the model developed presents some simplifications as it does not take into consideration other mechanisms which can contribute to the stress relieving as the recrystalization and grain growth phenomenon.

2. HEAT SOURCE

Accurate prediction of residual stress, distortion, and strength of welded structures require an accurate analysis of the thermal cycle. The importance of an adequate model for the weld heat source in the analysis of the thermal cycle has been emphasized by several investigators (Pavelik *et al.*, 1969; Goldak *et al.*, 1984; Ronda and Oliver, 2000). For

traditional welding process some authors represent the heat source as a geometric distribution of heat flux. Pavelic *et al.* (1969) suggested a Gaussian surface flux distribution disc. Friedman (1975) presents an alternative form for the Pavelic model expressed in a moving coordinate system, with an origin located at the center of the heat source. Goldak *et al.* (1984) presents a more accurate model comprising a non-axisymmetric three-dimensional “double ellipsoidal power density distribution” for moving weld heat sources based on a Gaussian distribution of power density in space. Goldak *et al.* (1984) studies reveal that the temperature in front of the heat source was not as steep as expected and the gentler gradient at the trailing edge of molten pool was steeper than experimental experience. Therefore, the Goldak model considers two ellipsoidal sources combined as show in Fig. 2a. The front half of the source in the quadrant of one ellipsoidal source, and the rear half is the quadrant of another ellipsoid.

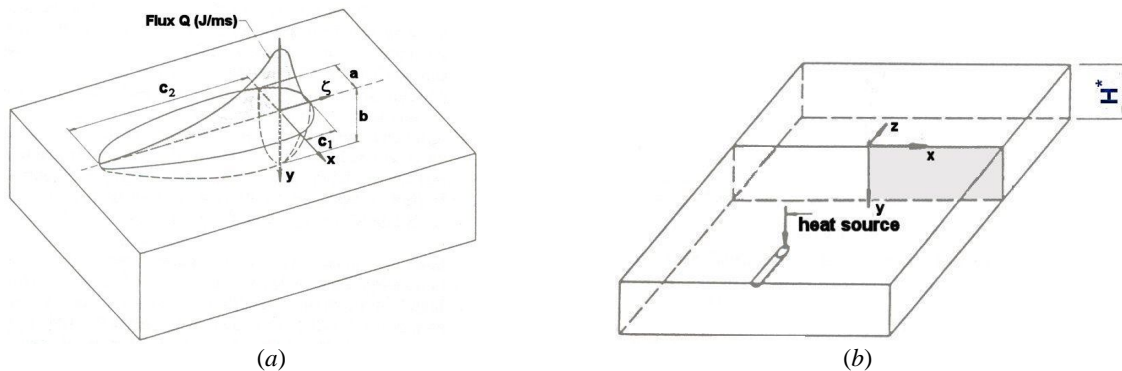


Figure 2. (a) Double ellipsoid power distribution heat source (b) Arrangement for the section bead on plate welds (Goldak, 1984).

The power density distribution of the source inside the ellipsoid becomes in according to:

$$q(x, y, \zeta, t) = \frac{6\sqrt{3}fQ}{abc\pi\sqrt{\pi}} e^{-3(x/a)^2} e^{-3(y/b)^2} e^{-(\zeta/c)^2} \quad (1)$$

where a , b , c ($c = c_1$ inside the front quadrant and $c = c_2$ inside the rear quadrant) are the semi-axis of the power density Gaussian distribution in an ellipsoid with center at $(0,0,0)$ and parallel to coordinate axes, x , y , ζ . The coordinate $\zeta = v(\tau - t)$, where v is the velocity of the heat source, t is the time and τ is a lag factor needed to define the position of the source at time $t = 0$. f is the fraction of heat ($f = f_f$ inside the front quadrant and $f = f_r$ inside the rear quadrant) and $Q = \eta VI$ is the welding energy input rate, where η is the heat source efficiency, V the voltage and I the current.

3. NUMERICAL MODEL

A bi-dimensional finite element thermo-elastoplastic model with temperature-dependent properties is developed to study the thermomechanical behavior of long welded plates. A bi-dimensional model is chosen in order to minimize the computational cost. For long plates, at a distance far from the edges, heat flow in the welding direction can be neglected (Goldak *et al.*, 1984). Considering these hypotheses, the model for a moving weld heat source of Eq. (1) and a symmetry condition at the plane yz (adiabatic condition), it is possible to reduce the analysis to the gray area region of Fig. 2b. This model can be applied to different geometries and welding conditions. Numerical simulations are performed with commercial finite element code ANSYS (Ansys, 2010), employing coupled thermal and mechanical fields element PLANE 13 for spatial discretization.

Figure 3a shows the plate section analyzed by the proposed model that represents the gray area region of Fig. 2b. To permit a better control on mesh discretization the plate section is divided in three areas (A1, A2 and A3) as shown in Fig. 3a. The boundary conditions and the mesh are shown in Figures 3b and 3c, respectively. Blue triangles represents displacement symmetry conditions whereas red arrows represents convection boundary conditions.

It is important to note that the proposed model presents some approximations that can influence the response and must be taken into account when analyzing the results. First, contrary to a real piece, the proposed model considers the presence of material in the region of weld deposition at all time instants (thus, before the weld deposition). Therefore, this region experiments first a temperature rise followed by a cooling. In a real welding process an empty region is first filled by weld material that is at a high temperature. Thus, this region is only submitted to a cooling stage. The second important approximation consists in the plane strain state adopted, which limits deformations in the z direction. In a real piece the surrounding material offers some degree of restriction in this direction, but not completely. Finally, the model does not compute the influence of phase transformations in residual stress. Some authors present models that consider

this effect (Zacharia *et al.*, 1995; Taljat *et al.*, 1998; Ronda and Oliver, 2000; Silva *et al.* 2004, 2005; Oliveira, 2004; Silva *et al.*, 2007; Silva, 2007; Oliveira *et al.*, 2010).

The finite element analysis is carried out in three stages: 1) *welding process*; 2) *cooling process* and 3) *post weld heat treatment (PWHT)*. In the *welding process stage*, the volumetric weld heat source flux distribution described by Eq. (1) is applied to the plate. In the *cooling process stage*, the weld heat source is removed and convection with the surrounding medium develops until a thermal equilibrium is reached. In the *PWHT stage*, a convection boundary condition considering a medium temperature equal to the furnace temperature is prescribed. For the two first stages a plane strain condition is adopted to simulate the restriction at z direction promoted by the material at lower temperature. In the *PWHT stage* a plane stress condition is adopted to simulate the stress relief at z direction and a null stress is obtained in this direction. The final mesh and the time step are defined after a convergence analysis (Fig. 3c). A non-linear transient thermo-elastoplastic analysis is conducted to obtain the time evolution of thermal and mechanical variables during the two stages of the welding process.

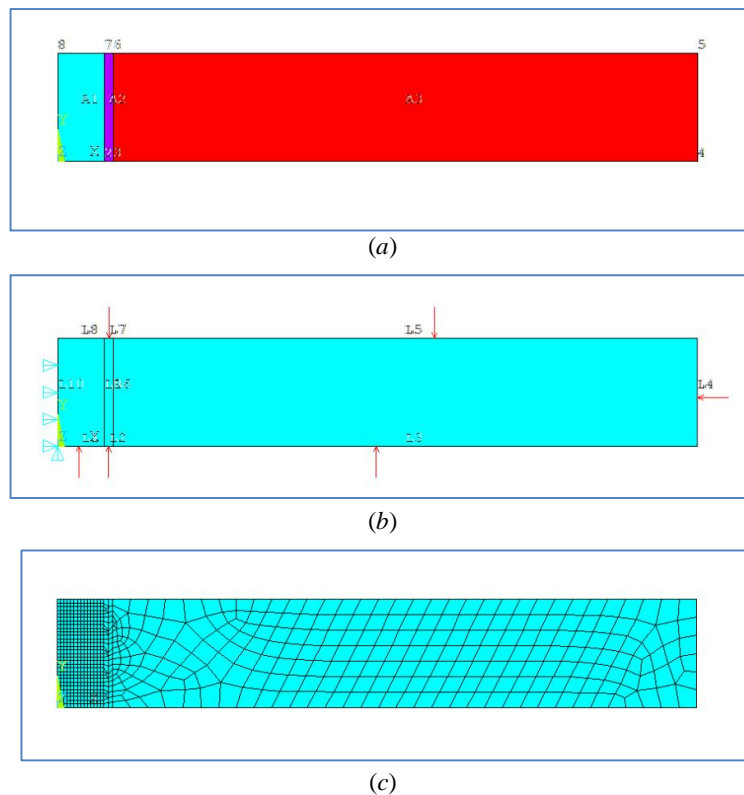


Figure 3. Finite element model. Geometry (a), boundary conditions (b) and mesh (c).

4. NUMERICAL SIMULATIONS


The proposed model is applied to the welding of a AISI 1045 steel plate by Metal Inert Gas (MIG) process. A bead on plate type welding is considered for a plate with a thickness, t , of 12.6 mm, and a length, L , of 150 mm. The numerical simulations developed considers thermal and mechanical temperature-dependent properties for AISI 1045 steel (Dogu, 2005) and the following parameters: $Q = 6769$ W, $v = 355$ mm/min, a density, ρ , of 7800 kg/m³, a convection coefficient, h , of 25 W/m², an air temperature, T_{∞} , of 25°C , an initial temperature, T_{ini} of 25°C , an austenitization and solidification temperatures of 730°C and 1500°C , respectively. Natural convection boundary conditions were used at plate free surfaces but at the symmetry plane yz . Temperature time evolution is assessed at 8 points positioned at the boundary of the weld region shown in Fig. 2. Different *PWHT* temperatures are analyzed to study the effect on residual stress relieve.

4.1. Heat source parameters calibration - Experimental analysis


Numerical simulations were developed to adjust heat source parameters of equation (1). Four thermocouples (type K), housed in a 1.5 mm diameter inconel cover, are introduced at half thickness plate deep holes in order to monitor the

temperature time history that is registered by a data acquisition system. Two thermocouples are positioned at the weld path line (TP1 and TP2) and two at a parallel line distant 21 mm from the weld path line (TP3 and TP4). Several numerical simulations were developed to adjust heat source parameters. An optimal configuration was obtained for $a = 13.75$ mm, $b = 0.504$ mm, $c_1 = 22$ mm, $c_2 = 44$ mm, $f_r = 0.6$, $f_r = 1.4$.

After the welding process, metallographic samples were prepared by the conventional technique of manual grinding and polishing followed by chemical etching with nital 2% reagent. Figure 4a shows a cross section macrography through thermocouples positions. Heat Affected Zone (HAZ) dimensions and the thermocouples holes are shown in the figure. Figure 4b shows the predicted FEM model HAZ. A good agreement between experimental and numerical results is observed. Results show that the HAZ presents a minimum thickness of 1 mm and the fusion pool presents a semicircle geometry with a 6.25 mm radius.

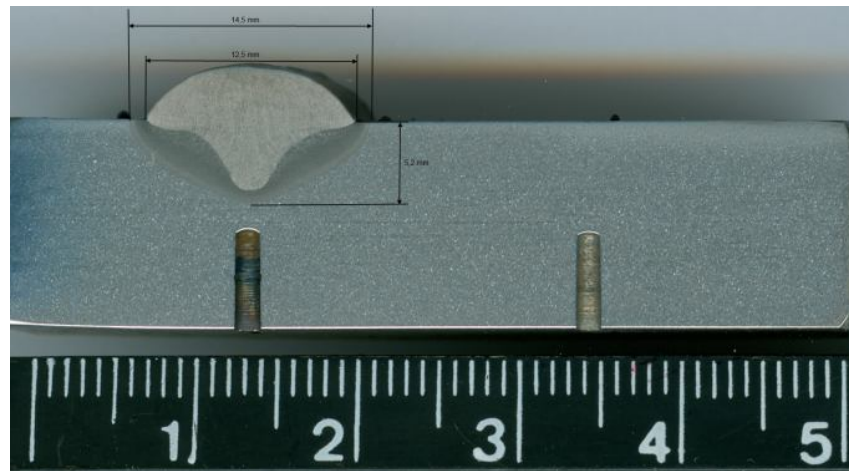

(a)

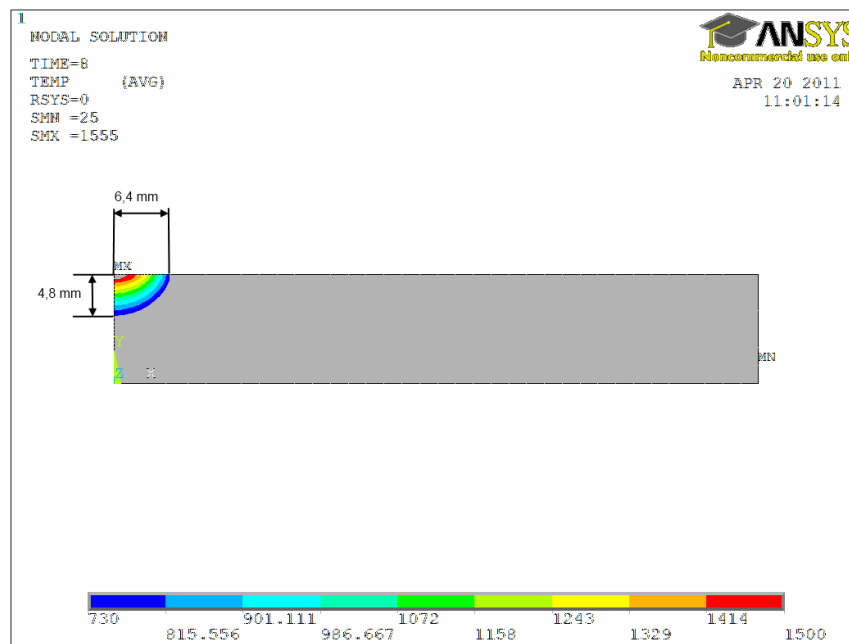

(b)

Figure 4. HAZ dimensions: (a) Macrograph Nital etch 2% and (b) HAZ temperature distribution predicted by the numerical simulation.

Figure 5 shows a comparison between temperature evolution obtained from experimental and numerical data. A good agreement is observed. It is important to note that numerical results are associated to an idealized point whereas experimental data is obtained from a thermocouple that measures temperature at a finite contact area. Therefore position errors are expected.

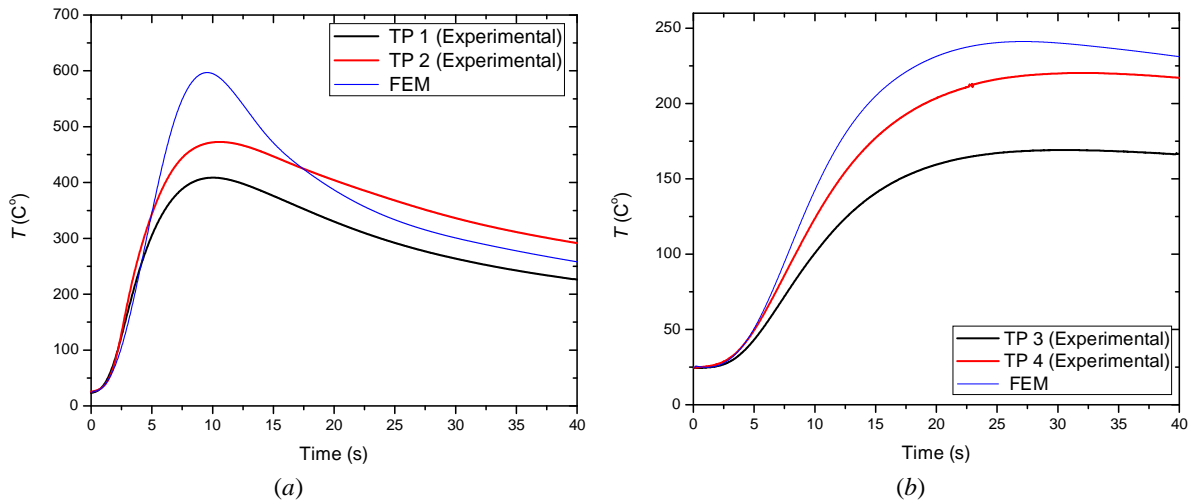


Figure 5. Temperature evolution obtained from experimental and numerical results. Thermocouples (a) TP1 and TP2 and (b) TP3 and TP4.

4.2. Effect of the PWHT temperature on residual stresses

First the model is applied to the welding process described in the last section considering a 600°C PWHT temperature. This value is usually adopted in literature.

Figures 6 and 7 show, respectively, temperature and stress time evolution for the 8 points shown in Fig. 3a. A peak temperature of approximately 2000°C is observed on the top surface at time instant $t = 6$ s. Stress time evolution presents a complex behavior during *welding* and *cooling* stages due to the strong temperature dependence of mechanical properties and the coupling between thermal and mechanical phenomena.

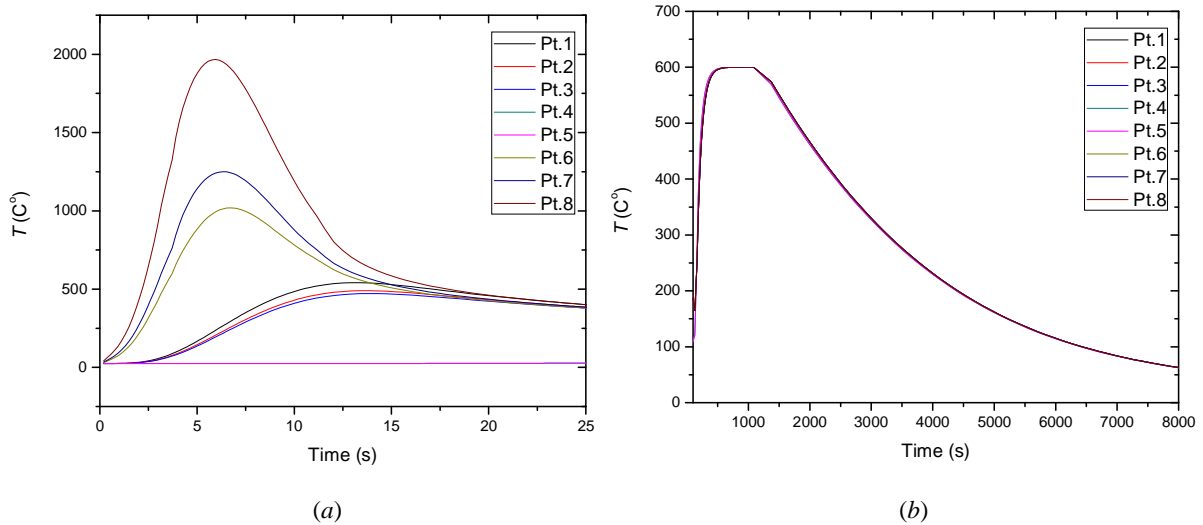


Figure 6. Temperature time evolution: (a) *welding* and *cooling* stages and (b) PWHT stage. 600°C PWHT temperature.


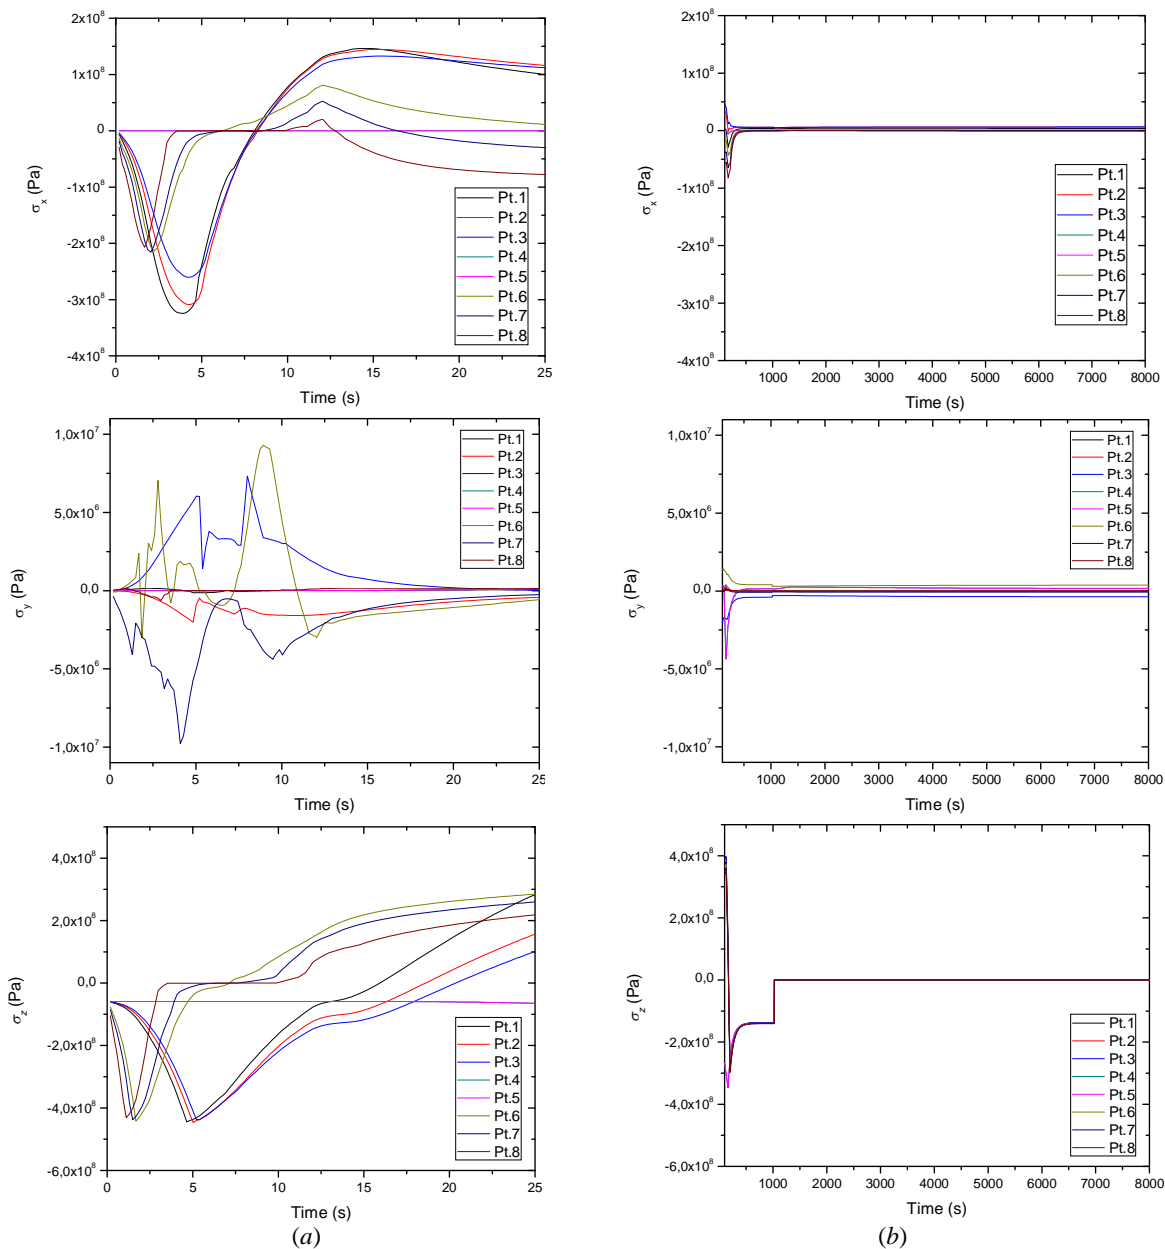


Figure 7. Stress time evolution: (a) welding and cooling stages and (b) PWHT stage.


Figures 8a-d shows the residual stresses distribution at the final of the *welding stage*, where a thermal equilibrium is achieved. The smallest stress values (in magnitude) are observed for y direction and the larger ones are observed for z direction (of room temperature yield strength magnitude). Figure 8e-g shows the residual stresses distribution at the final of the *PWHT stage*, where a thermal equilibrium is achieved. Stress in z direction presents the characteristic stress distribution reported in literature, with tensile stress near the welding region and compressive stress far from this region.

At this point the effect of *PWHT* temperature on residual stresses is considered. Figure 9 shows σ_x , σ_y and *von Mises* residual stresses after *PWHT* process. It can be observed that stress relieving occurs for *PWHT* temperatures higher than 400 °C. The amount of stress relieving rises up with *PWHT* temperature until a value of 600 °C, where stabilization is observed. This temperature is usually recommended in literature for *PWHT* processes.


The results obtained with the proposed model show that the behavior is very complex as it involves several coupled phenomena. Moreover, the proposed methodology can be used as a powerful tool to study the influence of the *PWHT* temperature and the welding parameters, like the heat input or the welding velocity, in the development of residual stresses in welded mechanical components. The finite element approach permits the direct application of the model to more complex geometries.

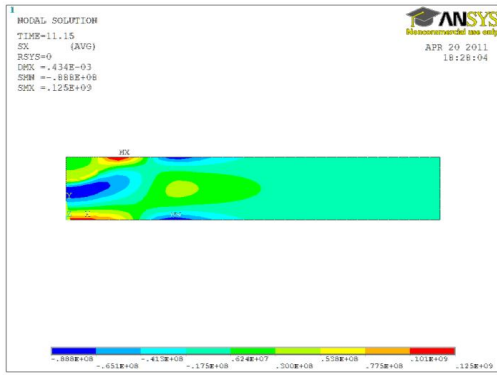


(a)

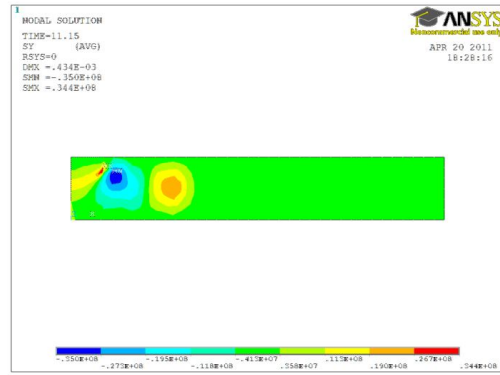


(b)

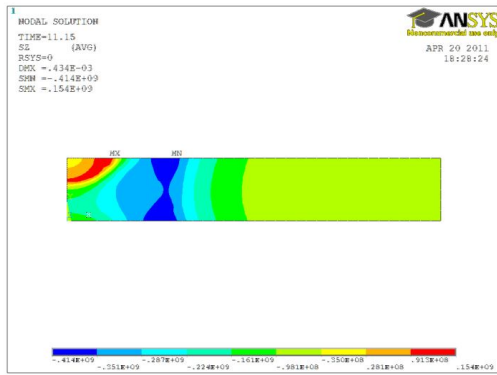


(c)

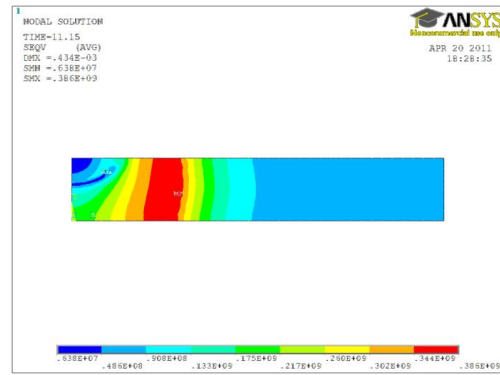


(d)

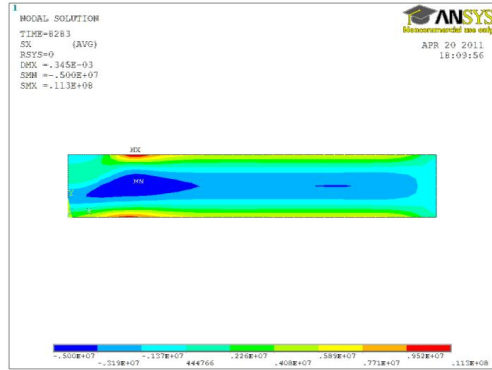

(e)

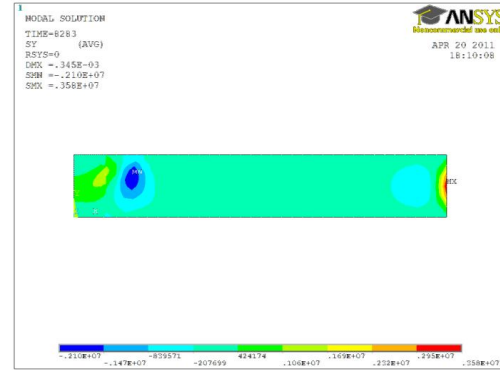

(f)

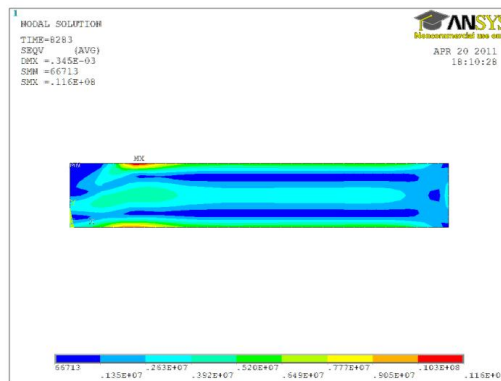

(g)

Figure 8. Residual stresses distribution after the *welding stage*: (a) σ_x , (b) σ_y , (c) σ_z and (d) σ_{eq} . 600°C PWHT. Residual stresses distribution after the *PWHT stage*: (a) σ_x , (b) σ_y , and (c) σ_{eq} . 600°C PWHT temperature.

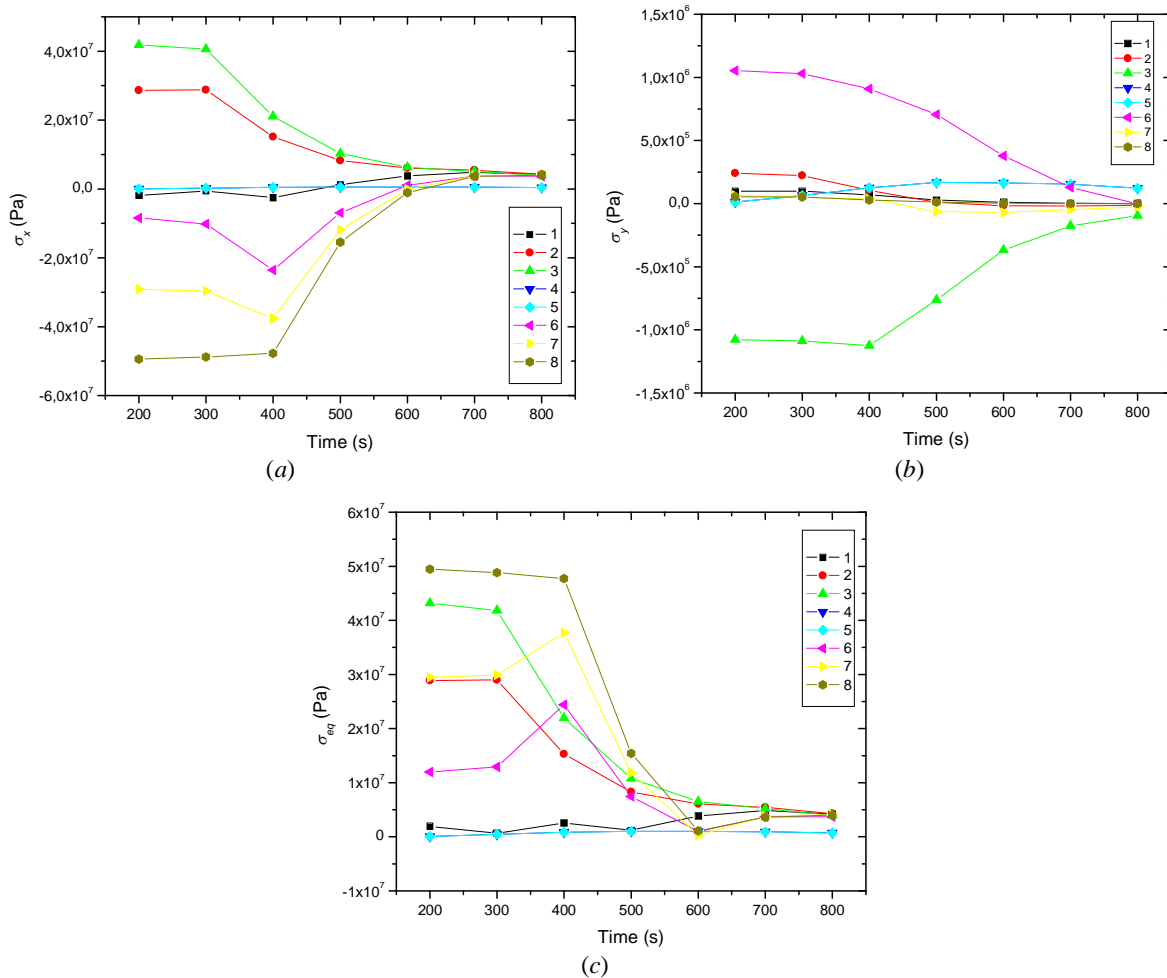


Figure 9. Residual stresses for different *PWHT* temperatures: (a) σ_x , (b) σ_y , and (c) *von Mises* equivalent stress.

It is important to note that the proposed model presents some approximations that can influence the response and must be taken into account when analyzing the results. First, contrary to a real piece, the proposed model considers the presence of material in the region of weld deposition at all time instants (thus, before the weld deposition). Therefore, this region experiments first a temperature rise followed by a cooling. In a real welding process an empty region is first filled by weld material that is at a high temperature. Also the bi-dimensional model uses plane strain and plain stress hypothesis conditions and it is not capable to capture adequately the stress behavior in the z direction. To deal with this a three-dimensional approach is necessary. Moreover, phase transformation can promote phase transformation induced strain (Silva *et al.*, 2005a, 2005b; Ronda and Oliver, 2000; Silva and Pacheco, 2005,2007; Silva, 2007) that can affect residual stresses in welded pieces.

5. CONCLUSION

The present contribution regards on modeling and simulation of post weld heat treatments (*PWHT*) for residual stress relieving in welded steel plates. A coupled bi-dimensional thermo-elastoplastic finite element model with temperature-dependent thermomechanical properties is developed to study *PWHT* of welded plates. The proposed model is applied to the bead on plate type welding of AISI 1045 steel plates. Numerical results indicate that the temperature levels of the *PWHT* affects the values of residual stresses. Stress relieving occurs for *PWHT* temperatures higher than 400 °C and the amount of stress relieving rises up with *PWHT* temperature until a value of 600 °C, where stabilization is observed. These results are in accordance with the literature for *PWHT* processes.

The proposed methodology can be extended to complex geometries and used as a powerful tool to study and adjust the *PWHT* process to minimize the residual stresses on welded mechanical components. Moreover, an experimental program must be established to validate the proposed model.

6. ACKNOWLEDGEMENTS

The authors would like to acknowledge the support of the Brazilian Research Agencies CNPq and CAPES.

7. REFERENCES

- ANSYS, 2010, "Ansys Manual", Release 12, Ansys Inc.
- Bang, I.W., Son, Y.P., OH, K.H., Kim, Y.P. and Kim, W.S., 2002, "Numerical Simulation of Sleeve Repairs Welding of In-Service Gas Pipelines", *Welding Journal*, pp. 273s–282s.
- Bezerra, A.C., Scotti, A. and Rade, D.A., 2006, "Efeito do Preaquecimento sobre as Tensões Residuais de Soldagem", *Soldagem & Inspeção*, Vol. 11, No. 1, pp. 54-61.
- Cao, X., Rivaux, B., Jahazi, M., Cuddy, J. and Birur, A., 2009, "Effect of pre- and post-weld heat treatment on metallurgical and tensile properties of Inconel 718 alloy butt joints welded using 4 kW Nd:YAG laser", *J Mater Sci*, v. 44, pp. 4557–4571.
- Costa, H.R.M., Lemos, M.M., Pacheco, P.M.C.L. e Aguiar, R.A.A., 2007, "Finite Element Analysis of Multipass Welded Steel Plates", COBEM 2007 - 19th International Congress of Mechanical Engineering, Brasília, DF.
- Dogu, D., 2005, "Finite Element Modeling of Stress Evolution in Quenching Process", M.Sc. Dissertation, Metallurgical and Materials Eng. Department, Natural and Applied Sciences of Middle East Technical University.
- Friedman, E., 1975; *Journal of Pressure Vessel Technology*, Trans ASME, Vol. 97, pp. 206-213.
- Kanga, H.T., Leeb, Y.-L. and Sun, X.J., 2007, "Effects of residual stress and heat treatment on fatigue strength of weldments", *Materials Science and Engineering A*, v. 497, pp. 37–43.
- Linnert, G.E., 1997, "Welding Metallurgy - Carbon and Alloy Steels", 3rd edition, American Welding Society.
- Goldak, J., Chakravarti, A. and Bibby, M., 1984, "A New Finite Element Model for Welding Heat Sources", *Metallurgical Transactions B*, Volume 15B, June 1984, pp. 299–305.
- Oliveira, W. P., 2004, "Modeling Quenching Process in Steel Cylinder Using Multi-Phase Constitutive Model", M.Sc. Dissertation, CEFET/RJ, in Portuguese.
- Oliveira, W.P., Savi, M.A., Pacheco, P.M.C.L. and Souza, L.F.G., 2010, "Thermomechanical analysis of steel cylinders quenching using a constitutive model with diffusional and non-diffusional phase transformations", *Mechanics of Materials*, v. 42, pp. 31–43.
- Paradowska, A.M., Price, J.W.H., Kerezi, B., Dayawansa, P. and Zhao, X.-L., 2010, "Stress relieving and its effect on life of welded tubular joints", *Engineering Failure Analysis*, v. 17, pp. 320–327.
- Pavelic, Z., Tanbakuchi, R., Uyehara, O.A. and Meyers, P.S., 1969, *Welding Journal Research Supplement*, Vol. 48, pp. 295s–305s.
- Ronda, J. and Oliver, G.J., 2000, "Consistent Thermo-Mechano-Metallurgical Model of Welded Steel with Unified Approach to Derivation of Phase Evolution Laws and Transformation-Induced Plasticity", *Comput. Methods Appl. Mech. Engrg.* Vol. 189, pp. 361-417.
- Silva, E. P., Pacheco, P. M. C. L. & Savi, M. A., 2004, "On the Thermo-Mechanical Coupling in Austenite-Martensite Phase Transformation Related to the Quenching Process", *Int. J. of Solids and Struct.*, v. 41, n. 3-4, pp. 1139-1155.
- Silva, E. P., Pacheco, P. M. C. L. & Savi, M. A., 2005a, "Finite Element Analysis of the Phase Transformation Effect in Residual Stresses Generated by Quenching in Notched Steel Cylinders", *Journal of Strain Analysis for Engineering Design*, v. 40, n. 2, pp. 151-160.
- Silva, R.M.B. and Pacheco, P.M.C.L., 2005, "Modeling Residual Stresses in Welded Steel Plates Using a Constitutive Model With Phase Transformation", *COBEM 2005 – 18th International Congress of Mechanical Engineering*, Ouro Preto, Minas Gerais.
- Silva, R.M.B., Pacheco, P.M.C.L., Oliveira, W.P. and Savi, M.A., 2005b "Modeling Residual Stresses in Welded Steel Plates Using A Constitutive Model With Diffusional Phase Transformations", *CILAMCE 2005 – XXVI Iberian Latin-American Congress on Computational Methods in Engineering*, Espírito Santo.
- Silva, R.M.B., 2007, "A Contribution to the Modeling the Welding Process of Steel Plates Using a Coupled Constitutive Model" (in portuguese), M.Sc. Dissertation, Mestrado em Tecnologia – CEFET/RJ.
- Silva, R.M.B. and Pacheco, P.M.C.L., 2007, "On the Thermomechanical Coupling Effects in the Welding of Steel Plates using a Constitutive Model", *COBEM-2007, 19th International Congress of Mechanical Engineering*.
- Taljat, B., Radhakrishnan, B., and Zacharia, T., 1998, "Numerical Analysis of GTA Welding Process with Emphasis on Post-solidification Phase Transformation Effects on Residual Stresses", *Mat. Science and Eng.*, V. A246, pp. 45–54.
- Teng, T. and Chang, P., 2004; "Effect of Residual Stresses on Fatigue Crack Initiation Life for Butt-Welded Joints", *Journal of Materials Processing Technology*, Vol. 145 pp. 325–335.
- Zacharia, T., Vitek, J.M, Goldak, J.A., Debroy, T.A., Rappaz, M. and Bhadeshia, H.K.D.H., 1995, "Modeling the Fundamental Phenomena in Welds", *Modeling Simul. Mater. Sci. Eng.*, Vol. 3, pp. 265-288.

8. RESPONSIBILITY NOTICE

The authors are the only responsible for the printed material included in this paper.