



DETERMINATION OF THERMAL CONDUCTIVITY OF EPOXY RESIN

Márcio Antonio Bazani

Vinicius Gomes Pereira

UNESP - Avenida Brasil 56, Centro, 15385000 – Ilha Solteira-SP
bazani@dem.feis.unesp.br / vinicius91294@aluno.feis.unesp.br

Amarildo Tabone Paschoalini

UNESP - Avenida Brasil 56, Centro, 15385000 – Ilha Solteira-SP
tabone@dem.feis.unesp.br

Abstract. *With the increase of technology in the electronics industry, new methods have emerged, resulting in smaller components and higher processing capacity. In contrast, problems related to rate of heat transfer of these components have been increasing and with this reduction in size, the temperature began to be an important variable to be observed in equipment. Normally, performance improvements, such as computers or racks of telephone exchanges, translate directly into greater heat dissipation of electronic devices that make up the device, and consequently, high rates of heat transfer. Thus, the cooling of electronic equipment gained paramount importance as the effect of increased power densities in micro-electronic equipment made available by advances in semiconductor technology. Because of this, whenever we face interesting challenges in finding a technique of removing heat more effectively for these high-tech applications, is one of those challenges, which underpin this research is to determine the properties of the constituent components of a new system cooling is a heat exchanger based on phase change of a fluid inert. There are a few examples: automotive radiator and air conditioning, cooling and optoelectronic LEDs. A heat exchanger is physically designed to enhance and to improve the surface in contact with the cooling fluid around it, like air. Approach air velocity, choice of material and surface treatment are some of the factors that influence the thermal resistance and thermal performance of these components. In this research, the epoxy resin with metallic charge, has lower thermal conductivity than aluminum, for example, however, it does not conduct electricity, getting great importance of electronic devices nowadays.*

Keywords: *conductivity, experimental, photoacoustic, emissivity, epoxy resin.*

1. INTRODUCTION

With the growth of the electronics industry, along with the field of telecommunications, new technologies have emerged through the requirement of customers and struggle to stay in the market. Since then, these industries started looking for smaller components and better and better, generating more phone functions in a rack, for example. With the increase in technology, the components are decreasing and at the same time, the problems increase. The temperature began to be an important variable to be observed in electronic equipment, because with the reduction of the components there was an increase in the rate of heat dissipation. Normally, performance improvements, such as computers or backstage of telephone exchanges, translate directly into greater heat dissipation of electronic devices that make up the equipment, and consequently, high rates of heat transfer.

Thus, the cooling of electronic equipment has gained considerable importance as a result of increased power densities in micro-electronic equipment made available by advances in semiconductor technology (Bar-Cohen, 1992).

Because of this, we always come across interesting challenges in finding a technique of removing heat more effectively for these high-tech applications.

One of these challenges, which is based this research consisted in determining the properties of the constituent component of a new cooling system, which is a latent heat exchanger of an inert fluid.

Examples of heat exchangers are: air conditioning and radiator inside a vehicle, cooling optoelectronic, electronic devices such as high-power lasers and light emitting diodes (LEDs).

A heat exchanger is physically designed to increase and improve the surface in contact with the cooling fluid around it, like air. Approach air velocity, choice of material and surface treatment are some of the factors that influence the thermal resistance and thermal performance of these components.

In this research, the heat exchanger was composed of an epoxy resin with metal loading, which has considerable thermal conductivity, however, does not conduct electricity, so far, a fact unprecedented in the market.

The fact that the resin is an innovative material made this research much more motivating, knowing also the great importance of electronic devices today, and the many applications that have cooling techniques.

Bazani, M. A, Pereira, V. G, Paschoalini, A. T.
Determination of Thermal Conductivity of Epoxy Resin

2. OBJECTIVE

Determining the thermal conductivity of an epoxy resin with metallic filler by the method of photoacoustic effect.

3. THE MATERIALS AND EXPERIMENTAL TECHNIQUE

To perform the measurements by photoacoustic effect, we used the method of open cell. The following materials were used in this project:

- Pre microphone amplifier type Tube Ultragain MIC100 Behringer;
- Electret microphone;
- Power Laser - He-Ne 8 mW of power;
- Amplifier tuned type Lock-in, (SRS 530);
- Mechanical light modulator "Chopper" Thorlabs;
- Photoacoustic cell configuration type open (OPC);
- Tektronix Oscilloscope.

In addition, we used a resin from a polyester adhesive that had as constituents, polyacids, drying agents, glycols and solvents, with it, the base resin for the manufacture of epoxy resin to metal loading.

The preparation of the resin was made towards a viable production scale if it were implemented in the industry. After the resin is mixed with the metal charge, the compound was subjected to intense agitation to ensure sample homogeneity. Furthermore, to ensure the concentration and composition of the metallic charge of the resin before performing the measurement tests, it was subjected to metallographic analysis (Fig. 6) by means of optical microscopes with viewing screens graduated in the Laboratory of microstructural characterization of block M1 of the Department of Mechanical Engineering.

Initially was used a charge of metallic copper powder with a density of 3g/cm^3 and then with a density of 2.7 g/cm^3 . This material was provided without cost, as material for study and research by the company Metalpó Indústria e Comércio Ltda.

The determination of thermal properties of the resin compositions was carried out similar to the metallic charge and the resin and two different grain sizes (different thickness) of the metal used and the procedure carried out in non-controlled temperature of approximately $30\text{ }^\circ\text{C}$.

Now, as a method to obtain the thermal properties of the sample, was used the photoacoustic, because the photothermal techniques, in particular the photoacoustic have shown to be extremely useful as methods of analysis of virtually any type of material with a very characteristic important: they are non-destructive techniques.

They bring together a large group of experimental methods based on the conversion of light energy into heat. In this technique, the light energy falls transiently or periodically on the investigated material (epoxy resin with metal loading), being part of this energy, absorbed and partly transformed into heat as a result of processes without excitation of atomic energy levels and molecular .

The temperature of the material varies with the same frequency as the incident radiation, leading to variation in parameters such as sample refractive index, thermal conductivity and thermal diffusivity. The diffusivity (thermal conductivity as well) is a parameter that gives a measure of how heat propagates into the sample and has a unique value for each material, hence its importance (Olenka, 2003).

From the absorption of radiation by the material, a specific sensor detects the change in the behavior of this material, where many different effects can occur in the sample or in their neighborhoods.

In the different methods of measuring the properties by the photoacoustic effect, the experiment can be prepared to obtain a thermal property: α_s , thermal diffusivity, k , the thermal conductivity and heat capacity per unit volume ρC_p . For review one of these properties is considered that there is a dependence of photoacoustic signal with the modulation frequency of the light falling on the sample. In the method of open, cell can be monitored the dependence when the sample passes from a thermally thin regime to a thermally thick. In Figure 1 we have a scheme of this method.

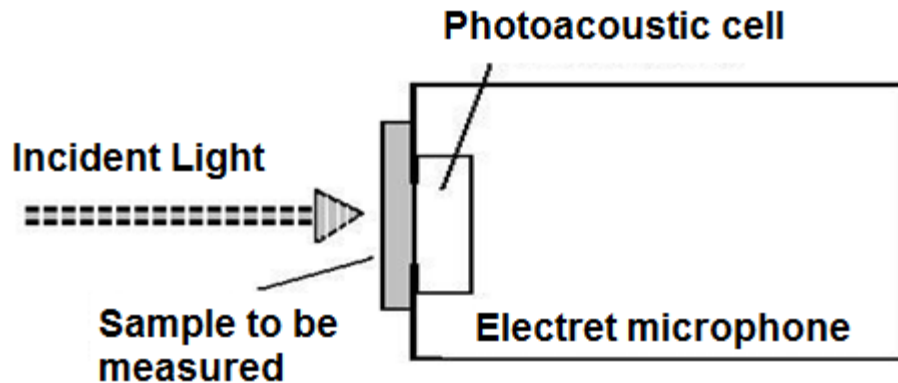


Figure1. Method of measurement of open cell (OPC)

The theory of the photoacoustic effect provides the dependence of the signal amplitude and its phase depending on the modulation frequency. Insofar as the modulation frequency is increased the thermal diffusion length (μ) decreases, because of this, the sample passes from thermally thin regime ($\mu_s \gg l_s$) to a thermally thick ($\mu_s \ll l_s$) and l_s is the thickness of the sample (Olenka, 2003). We can observe that the dependence on thermally thin regime ($\mu_s \gg l_s$) for optically opaque samples, the amplitude of the photoacoustic signal has the functional dependency on frequency in order:

$$S \propto f^{(-\frac{3}{2})} \quad (1)$$

For a thermally thick sample the amplitude of the photoacoustic signal has a functional dependence on frequency in order:

$$S \propto \frac{1}{f} e^{-b\sqrt{f}} \quad (2)$$

with:

$$b = l_s \left(\frac{\pi}{\alpha_s} \right)^{\frac{1}{2}} \quad (3)$$

Of parameter b and knowing the thickness of the sample l_s we evaluate the thermal diffusivity of the material. In dependence of the transition between these two regimes, have a value at which the thermal diffusion length equals the thickness of the sample $\mu_s = l_s$. This occurs at a certain frequency. In this case the parameter of thermal diffusivity can be evaluated in light of this frequency f_c at the transition point by the relation:

$$\alpha_s = \pi f_c l_s^2 \quad (4)$$

3.1 Method of measuring

For this method a sample is considered optically opaque wherein the periodic heating by light incident on the sample is performed in the sample-air interface resulting acoustic effect piston. The sample was placed directly on the microphone. To ensure the coupling microphone-sample, was passed up a thin layer of silicone grease on the surface of the microphone, which in addition to helping the coupling function is to isolate the chamber air photoacoustic that the external environment. Before the start of the experiments, some standard procedures in the measurement equipment were taken. First, the set light of He-Ne laser for focussing it at right angles on the sample surface towards the bore and the microphone, as can be seen in Fig. 2 and Fig. 3. Furthermore, it is necessary that the sample surface has low reflectance, as this measurement process is by absorption of light and heat generation, resulting that the larger the absorption, the greater the amplitude of the photoacoustic signal. Because the surface material has a high degree of reflectivity (very common in metals), it was necessary the deposition of a thin layer of black ink. The adopted to carry out the measurements, all samples had their surfaces on the side of excitation, covered by a thin layer of black ink for better heat absorption.

Bazani, M. A, Pereira, V. G, Paschoalini, A. T.
Determination of Thermal Conductivity of Epoxy Resin



Figure 2. Experimental apparatus off.



Figure 3. Experimental apparatus on.

When starting the measurements, was waited for the stabilization of the amplitude and phase of the photoacoustic signal. The phase of the photoacoustic signal was then adjusted in the lock-in to 180 °. This is done so that there is no phase inversion (-180 ° to 180 °) in the course of action and that a standardization in measurements can be made.

Subsequently set up a frequency modulation initial 20Hz from which we made a sweep from 20Hz to 300Hz. After, the filters were activated until the frequency of 60Hz and then reactivated at a frequency of 120Hz, which are the first two harmonics of the frequency range analyzed.

To perform these measurements, was developed an program for data acquisition in LabView ® platform as shown in Fig. 4. With this program, as there is a variation in the frequency manually, the program stores the generated points and automatically generates a curve of the photoacoustic signal by frequency modulation.

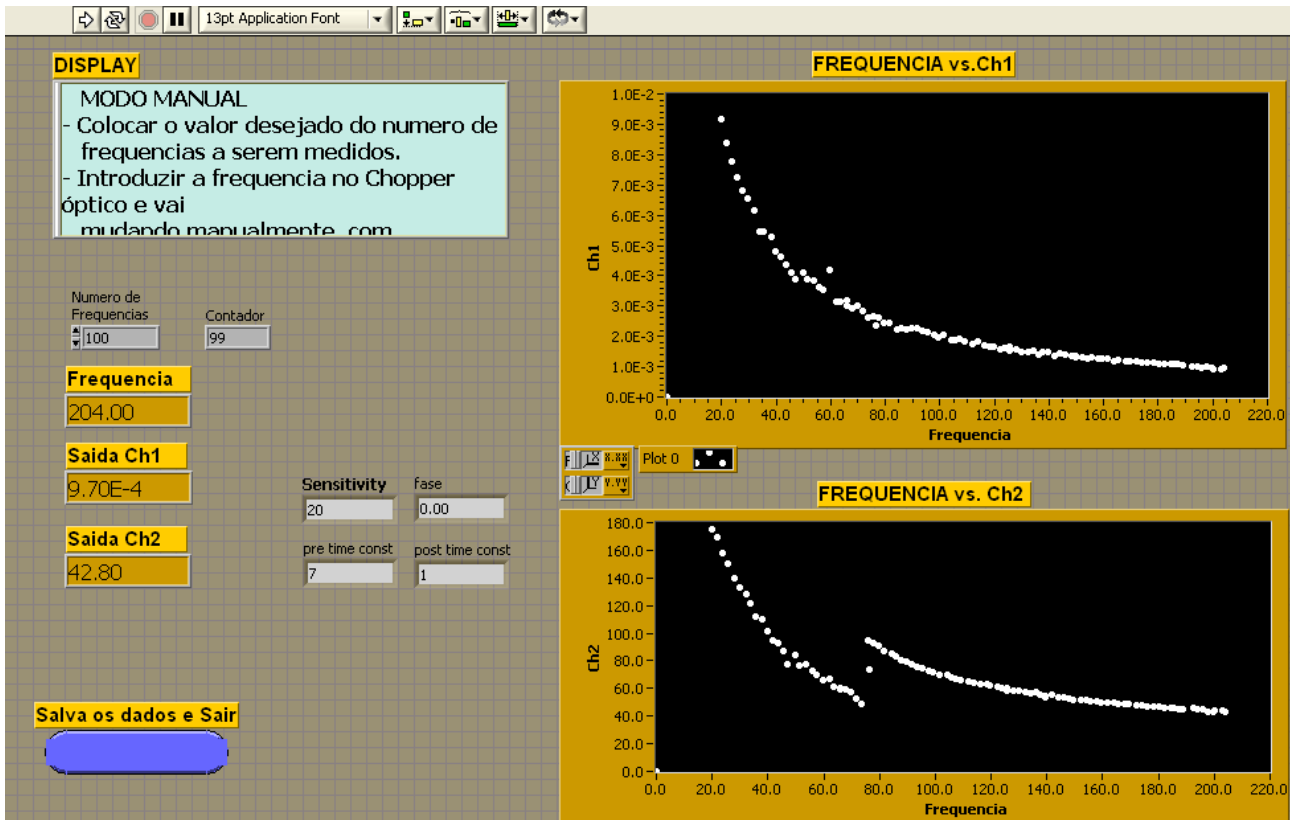


Figure 4. Display program data acquisition in LabView (in Portuguese)

Finally, after detection and storage of components of intensity and phase of the photoacoustic signal in their respective frequencies, these data were analyzed (Prandel, 2009).

4. RESULTS AND DISCUSSION

First, to check the response of the microphone was carried out a scan on a sample of carbon paper, which is known and depends on the inverse of the modulation frequency. The result was satisfactory. After this check, was given start measurements on the first sample that was a resin which had copper powder density 3g/cm³.

Then with the calibrated microphone, can be traced the graph of intensity's logarithm against the frequency's logarithm, allowing indicate the frequency region in which there is a predominance of diffusion behavior thermally thick. Applying the logarithm function in both members of Eq. (5) is obtained from the linear Eq. (6) for adjusting the amplitude and phase of the photoacoustic signal:

$$S \cdot f = e^{b\sqrt{f}} + C \quad (5)$$

$$\ln(S \cdot f) = b\sqrt{f} + C \quad (6)$$

Bazani, M. A, Pereira, V. G, Paschoalini, A. T.
Determination of Thermal Conductivity of Epoxy Resin

In order that the coefficients “C” (constant) and “b” were obtained in the experimental graph of $\text{Ln}(S.f)$ versus $f^{\frac{1}{2}}$, and S is the signal and f the frequency (Fig. 5). Knowing the sample thickness (l_s), the thermal diffusivity of the sample α_s was obtained by the equation (7):

$$b = l_s \left(\frac{\pi}{\alpha_s} \right)^{\frac{1}{2}} \quad (7)$$

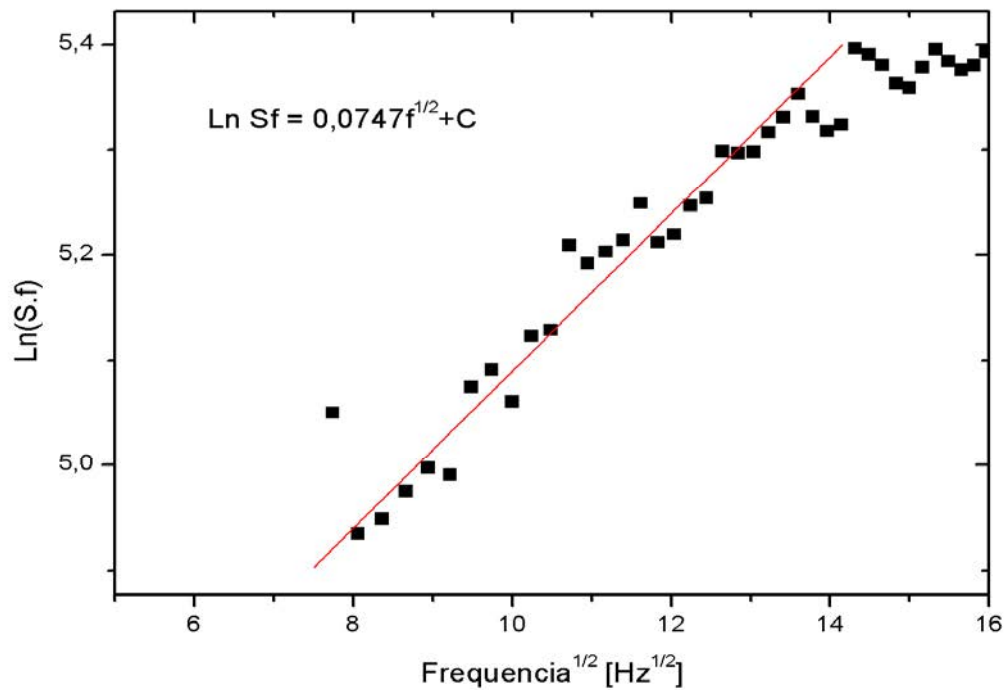


Figure 5. $\text{Ln}(S.f)$ versus $f^{\frac{1}{2}}$ for the first sample.

Thus, the values of the thickness of the sample ($l_s = 0.3 \times 10^{-3}$ m), and the b value found from the graph, there was obtained a value of diffusivity equal to 0.5×10^{-4} m²/s. With this value according to Eq. (8) was obtained value of thermal conductivity for the sample:

$$k = \rho \alpha C_p \quad (8)$$

The value of $k = 69,75 \frac{W}{mK}$ was obtained for a value of ρC_p equal to $1395 \times 10^3 \text{ J/m}^3 \text{ K}$ obtained experimentally according to the hot wire (Fukushima, 2011).

For the second sample that was a resin which had copper powder density 2.73 g/cm^3 , the initial calibration was carried into the microphone using an aluminum sample of the same dimensions of the sample of resin (0.2×10^{-3} m). The calibration curve is shown in Fig. 6.

22nd International Congress of Mechanical Engineering (COBEM 2013)
November 3-7, 2013, Ribeirão Preto, SP, Brazil

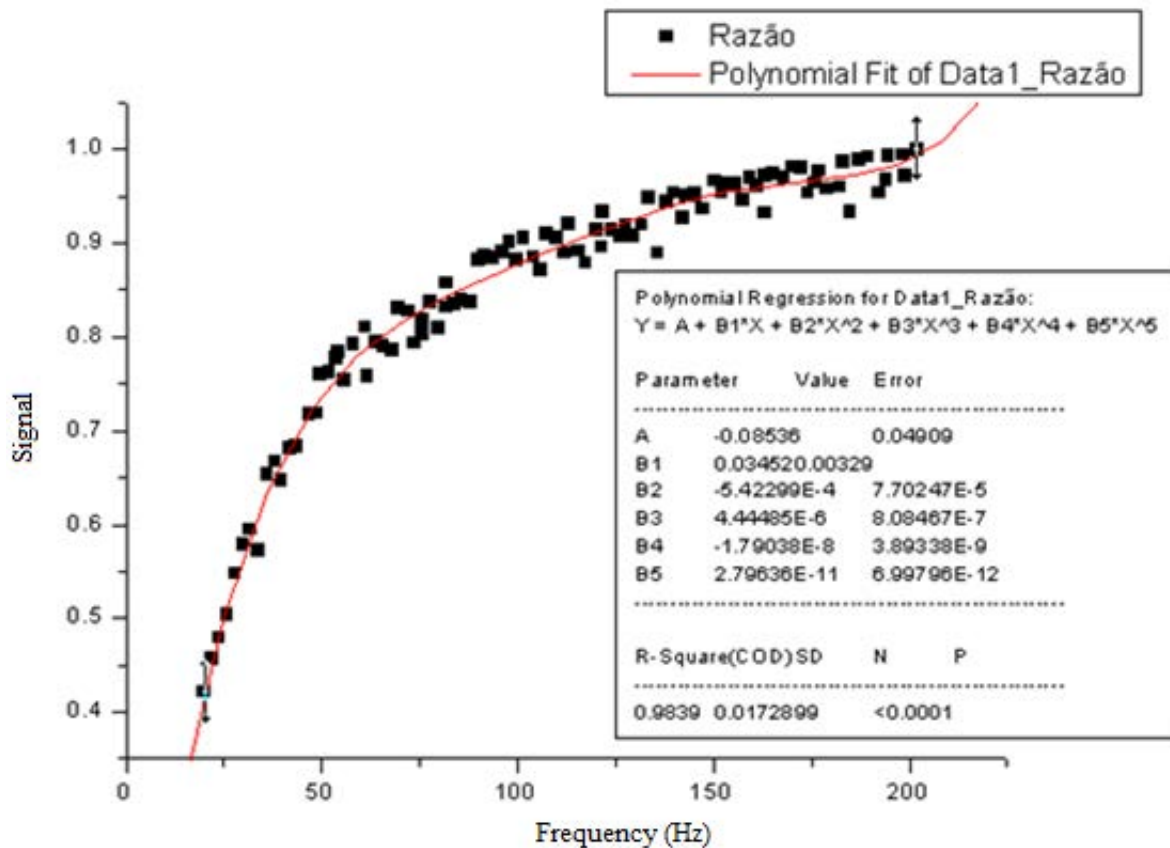


Figure 6. Calibration curve of the microphone for the sample of aluminum.

Then, with the calibrated microphone, was repeated the same procedure performed in sample 1. Thus, it can be traced the graph of intensity's logarithm against the frequency's logarithm, allowing indicate the frequency region in which there is a predominance of diffusion behavior thermally thick. Applying the logarithm function in both members of Eq. (5) is obtained from the linear Eq. (6) for adjusting the amplitude and phase of the photoacoustic signal.

In order that the coefficients C (constant) and b were obtained in the experimental graph of $\ln(S.f)$ versus $f^{\frac{1}{2}}$ (Fig. 7). Knowing the sample thickness (l_s), the thermal diffusivity of the sample α_s was obtained again by using Eq. (7).

Bazani, M. A, Pereira, V. G, Paschoalini, A. T.
Determination of Thermal Conductivity of Epoxy Resin

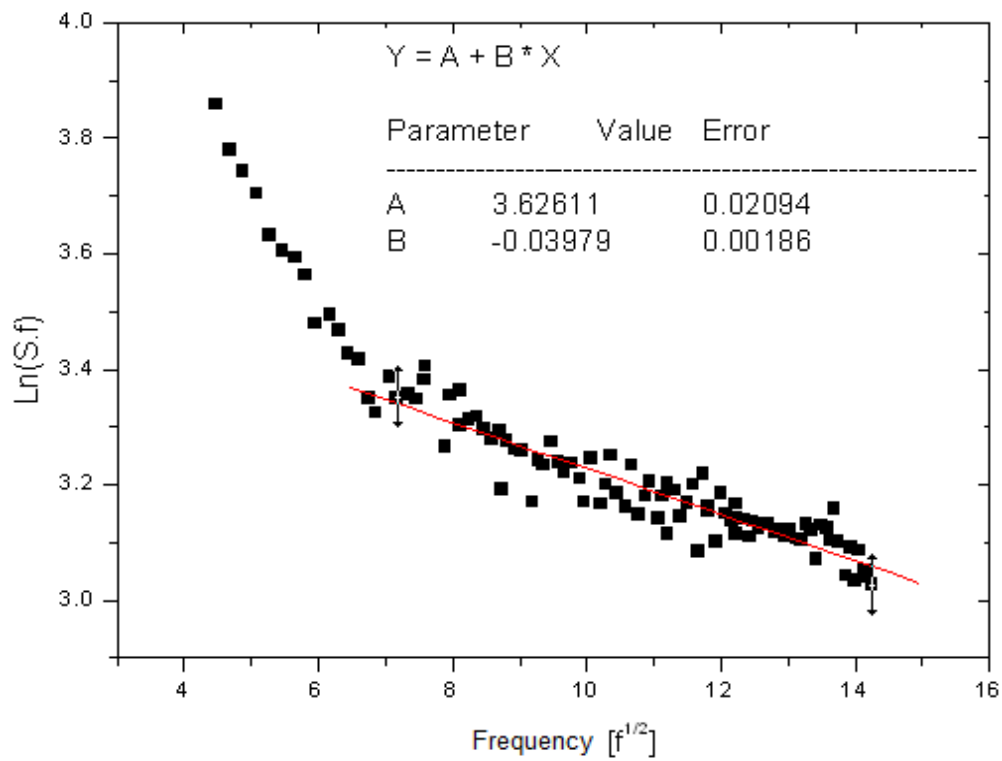


Figure 7. Graph of $\text{Ln}(S.f)$ versus $f^{\frac{1}{2}}$ for the first sample.

With thickness values of sample 2 ($l_s = 0.2 \times 10^{-3}$ m), and found the value of b in the graph, gave a diffusivity value of $0.79 \times 10^{-4} \text{ m}^2 / \text{s}$. With this value according to Eq. (8), the value of thermal conductivity for the sample was obtained.

Thus, the value of $k = 110,3 \text{ W/mK}$ was obtained for the second sample with a value equal to $1390 \times 10^3 \text{ J/m}^3\text{k}$ to ρC_p , obtained experimentally according to the hot wire (Fukushima, 2011).

Furthermore, it is also known that the porosity, size, shape and particle size distribution affect the physical and mechanical properties of the materials in its manufacture (Prandel, 2009). In the case of such resin predominates to the metallic charge, it only being coated with a polymeric layer as shown in Fig. 8.

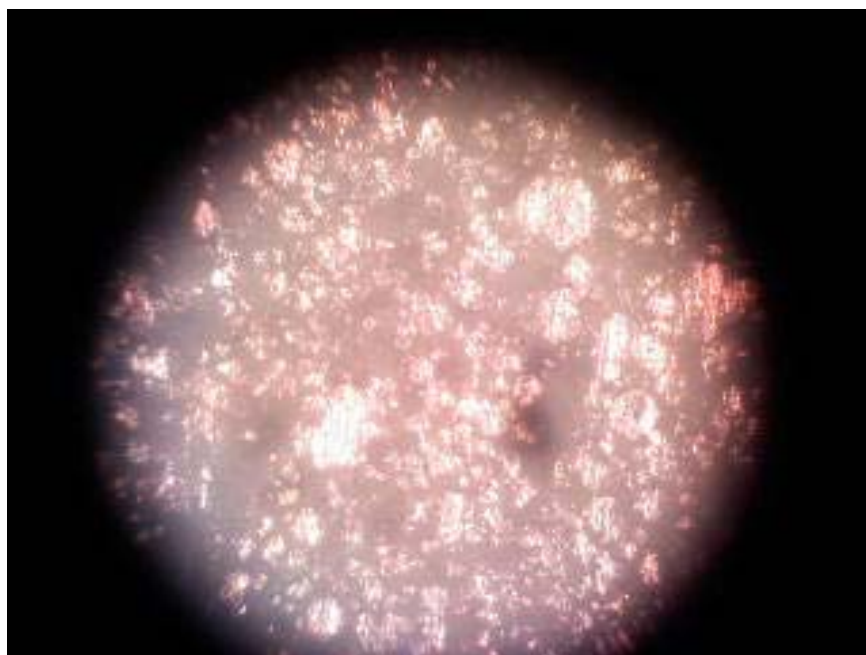


Figure 8. Epoxy Resin in micrographic analysis.

5. CONCLUSIONS

The photothermal techniques, in particular the photoacoustic, have proved extremely useful as methods of analysis of virtually any type of material. One of the important features of this technique is that they are non-destructive.

The temperature of the material varies with the same frequency as the incident radiation, leading to variation in parameters such as sample refractive index, thermal conductivity and thermal diffusivity. The diffusivity and thermal conductivity is a parameter that allows a measure of how heat propagates into the sample and has a unique value for each material, hence its importance (Olenka, 2003).

The data acquisition was done using a program developed in Labview platform and with the data obtained, was possible to build graphs with the help of software Origin ® [6] and thus was possible to determine their characteristic equations and analyze the behavior of the samples in ambient conditions, and finally possible to find conductivity values for each resin sample type.

The values found were satisfactory compared to the values found in the literature (Araujo and Rosenbergr, 1976) and (Konzelmann *et al.*, 2008) since the resin does not conduct electricity and to which the resin had copper powder density of 3g/cm³ was obtained a thermal conductivity of 69,75W/mK and the resin which had copper powder density of 2.7 g/cm³ and a thickness of 0.2 x10⁻³m was obtained a thermal conductivity of 110,3 W/mK.

This is due to the fact that the resin present in the metal charge is surrounded by a polymeric layer as shown in Fig. 8. This feature prevents the passage of electric current, however, does not prevent the transfer of heat, being beneficial in cooling applications of electronic and telecommunications equipment requiring heat exchangers which are only electrical insulators.

This electrical insulating property can be proven in the lab after lab tests are performed with an electrometer, which was obtained by an electrical resistance of approximately 39GigaOhm.

Furthermore, the results are reliable because the parameters were calculated by means of the acquisition of data demonstrated error 0,186%, which proves that the method used OPC was useful and effective.

6. ACKNOWLEDGEMENTS

I thank my advisor Marcio Antonio Bazani for their confidence in me and the opportunity to have begun to develop this research with him. I also thank the teachers Amarildo Tabone Paschoalini and Victor Ciro Solano Reynoso for their support and help in the collection of data and development of software, the entire laboratory staff LABSIM and Laboratory of Physical and Chemistry of the Faculty of Engineering of Ilha Solteira for making available the equipment and physical space for the experiments could be performed.

7. BIBLIOGRAPHIES

- Araujo, FFT and Rosenbergr, 1976. "The thermal conductivity of epoxy-resin/metal-powder composite materials from 1.7 to 300k". In *The Clarendon Laboratory*, University of Oxford, Oxford OX1 3PU.
- Bar-Cohen, A., 1992. "State-of-the-art and trends in the thermal packaging of electronic equipment". In *J. Electron. Packag.*, vol. 114/257, Sept.1992.
- Fukushima, J. 2011, "Determinação do Calor específico -Método do Fio Quente"- *Scientific Initiation* In FEIS - UNESP Ilha Solteira 2011.
- Konzelmann, S., Hoffmann, C., Merte, R. and Peier, D., 2008. "Thermal and Electrical Properties of Aluminum Nitride Filled Epoxy-resin Compound" - *University of Dortmund, Institute of High-Voltage-Engineering and EMC Friedrich-Wohler-Weg 4, D-44227 - Dortmund, Germany.*
- Olenka, L., 2003. "Utilização de técnicas Fototérmicas na Determinação de propriedades ópticas e Térmicas de polímeros impregnados". - *Programa de Pós Graduação em Física, Universidade Estadual de Maringá*, UEM, 2003. Thesis (Ph.D.) Maringá.
- Prandel, L.V. 2009, "Implementação da Técnica de Fotoacustica de Celula Aberta para obtenção da difusividade térmica de metais(OPC)"- *Programa de Pós Graduação em Ciências, Universidade Estadual de Ponta Grossa- UEPG*, 2009 Thesis (Master), Ponta Grossa.

8. RESPONSIBILITY NOTICE

The authors are the only responsible for the printed material included in this paper.