

FATIGUE CRACK GROWTH OF BIFURCATED CRACKS UNDER NEAR-THRESHOLD CONDITIONS

Antonio Carlos de Oliveira Miranda, amiranda@tecgraf.puc-rio.br

Marco Antonio Meggiolaro, meggi@puc-rio.br

Jaime Tupiassú Pinho de Castro, jtcastro@puc-rio.br

Luiz Fernando Martha, lfm@puc-rio.br

Pontifical Catholic University of Rio de Janeiro, Rua Marquês de São Vicente 225 – Gávea, Rio de Janeiro, RJ, 22453-900, Brazil

Abstract. Fatigue crack bifurcation is a mechanism that can quantitatively explain retardation effects even when plasticity induced crack closure is not observed. Analytical solutions have been obtained for the reduction in the SIF of some bifurcated cracks, however numerical methods are the only means to predict the subsequent curved propagation behavior. Empirical equations have been proposed by the authors to calculate the process zone size and SIF along the curved crack branches, based on extensive FE calculations on a CT specimen. The equations are a function of the bifurcation angle, ratio between the branch sizes, and material crack growth exponent. The equations can also include the interaction with other retardation mechanisms through the use of the limiting value K_{max}^* (or any other propagation threshold quantity K_{PR}) of the Unified Approach. In this work, the increase in fatigue life associated with bifurcated cracks under near-threshold conditions is studied. The equations presented in are re-evaluated for other specimen geometries using a specially developed FE program, validated from 4340 steel ESE(T) specimens. This program calculates the path and associated SIF along the bifurcated crack path. The results show a competition between the effects of bifurcation and other retardation mechanisms under near-threshold conditions. Even though a higher K_{max}^* or K_{PR} level would lead to a slower crack growth rate, the smaller SIF range can lead to a premature arrest of the shorter branch, resulting in a smaller bifurcation process zone. The presented fatigue life calculation methodology can be used to predict the propagation behavior of bifurcated cracks in an arbitrary structure.

Keywords: Crack retardation model, Bifurcated cracks, Finite elements, Life prediction

1. INTRODUCTION

Fatigue cracks can significantly deviate from their Mode I growth direction due to the influence of overloads, multi-axial stresses, micro structural inhomogeneities (such as inclusions, grain boundaries and interfaces), or environmental effects, generating crack kinking or branching (Lankford and Davidson, 1981). A fatigue crack deviated from its nominal Mode I plane induces mixed-mode near-tip conditions even if the far-field stress is pure traction. For instance, a pure Mode I stress intensity factor (SIF) K_I locally induces Modes I and II SIF k_1 and k_2 near the longer branch b of a bifurcated crack and k_1' and k_2' near the shorter c one. The equivalent SIF K_b and K_c of the longer and shorter branches, calculated respectively from (k_1, k_2) and (k_1', k_2') using e.g. the $\sigma_{\theta max}$ criterion (Erdogan and Sih, 1963), can be considerably smaller than that of a straight crack with the same projected (on the original crack plane) length. Therefore, such branching can retard or even arrest subsequent crack growth (Suresh, 1983).

Some analytical solutions have been obtained for the SIF of kinked and branched cracks, but it is generally recognized that it is very difficult to develop accurate analytical solutions for their complex propagation behavior (Karihaloo, 1982). Therefore, numerical methods such as Finite Elements (FE) and Boundary Elements (BE) are the only practical means to predict the propagation behavior of branched cracks (Pärletun, 1979). To accomplish that, a specially developed interactive FE program named Quebra (meaning fracture in Portuguese) is used (Miranda et al., 2002).

2. PROPAGATION OF BRANCHED CRACKS

The growth of branched cracks is studied using the Quebra program to model a C(T) specimen with width $w = 32.0mm$, crack length $a = 14.9mm$, and a very small bifurcation with angle 2θ ranging from 40° to 168° , initial longer branch length $b_0 = 10\mu m$ and initial shorter branch lengths ranging from $c_0 = 5\mu m$ to $10\mu m$. A fixed crack growth step of $\Delta b = 3\mu m$ (or $1\mu m$ during the first propagation steps) is considered for the propagation of the longer branch b . This growth step is calculated in the direction defined by the $\sigma_{\theta max}$ criterion (Erdogan and Sih, 1963). Due to the differences in the SIF and crack growth rate, a growth step Δc smaller than Δb is expected for the shorter branch. This smaller step is obtained assuming a crack propagation law that models the first two growth phases,

$$\frac{da}{dN} = A \times [\Delta K - \Delta K_{th}(R)]^m \quad (1)$$

where A and m are material constants and $\Delta K_{th}(R)$ is the fatigue crack propagation threshold at the $R = K_{min}/K_{max}$ ratio of the test. If ΔK_b and ΔK_c are respectively the stress intensity ranges of the longer and shorter branches, then the growth step Δc of the shorter branch c should be

$$\Delta c = \Delta b \cdot \left(\frac{\Delta K_c - \Delta K_{th}(R)}{\Delta K_b - \Delta K_{th}(R)} \right)^m \quad (2)$$

Interestingly, the ratio between the propagation rates of the two branches is independent of the material constant A . In this analysis, the exponent m is assumed to be 2.0, 3.0, and 4.0, which are representative for the range of the measured exponents for structural alloys. A similar expression can be obtained if other crack retardation mechanisms are considered, through Lang and Marci's propagation threshold K_{PR} (Lang and Marci, 1999) with A and m parameters fitted for each considered load ratio R :

$$\Delta c = \Delta b \cdot \left(\frac{K_{max,c} - K_{PR}}{K_{max,b} - K_{PR}} \right)^m \quad (3)$$

where $K_{max,b}$ and $K_{max,c}$ are the maximum SIF of the longer and shorter branches respectively. Or else this threshold K_{PR} can be replaced by a limiting value K_{max}^* , the threshold of the maximum of Sadananda and Vasudevan's Unified Approach (Sadananda et al., 2001), which assumes that a crack can propagate only when $\Delta K > \Delta K_{th}^*$ and $K_{max} > K_{max}^*$, where $\Delta K_{th}^* = \Delta K_{th}(R \rightarrow 1)$.

Both the crack path and the associated SIF along each branch are obtained using the **Quebra** program. Several calculations were performed for different values of the exponent m , bifurcation angle 2θ , relation c_0/b_0 , and SIF, considering or not the effect of K_{PR} , as described next.

3. BRANCHED CRACK PROPAGATION WITH $K_{PR} = 0$

In this section, the propagation behavior of branched cracks is studied using FE but neglecting any retardation mechanism other than the bifurcation itself (i.e. assuming $K_{PR} = 0$). Figure 3 shows the crack paths obtained from the FE analyses of bifurcated cracks with $2\theta = 130^\circ$ and $c_0/b_0 = \{0.5, 0.8, 0.95, 1\}$, considering $m = 2$ and $K_{PR} = 0$. The dashed lines show the theoretical propagation behavior of a perfectly symmetric bifurcation ($c_0/b_0 = 1$). In this case, the retardation effect would never end because both branches would propagate symmetrically without arresting. Clearly, such behavior is not observed in practice, since the slightest difference between b_0 and c_0 would be sufficient to induce an asymmetrical behavior. Figure 1 also shows that lower c_0/b_0 ratios result in premature arrest of the shorter crack branch, leading to smaller retardation zones. Also, the propagation path of the longer branch is usually restrained to the region within the dashed lines, while the shorter one is "pushed" outside that envelope due to shielding effects.

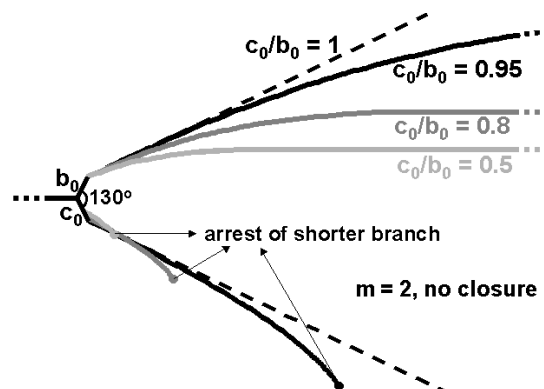


Fig. 1. Bifurcated crack paths for several c_0/b_0 ratios ($K_{PR} = 0$).

The size of the retardation zone can be estimated from the ratio b_f/b_0 , where b_f is the value of the length parameter b of the longer branch (measured along the crack path) beyond which the retardation effect ends. The ratio b_f/b_0 is then calculated through FE propagation simulations for all combinations of $c_0/b_0 = \{0.5, 0.8, 0.9, 0.95\}$, $2\theta = \{40^\circ, 80^\circ, 130^\circ, 168^\circ\}$ and $m = \{2, 3, 4\}$, and fitted by the proposed empirical function:

$$\frac{b_f}{b_0} = \exp\left(\frac{2\theta - 30^\circ}{56 + 17 \cdot (m-2)^{2/3}}\right) / (1 - c_0/b_0)^{(12-m)/20} \quad (4)$$

The FE-calculated equivalent SIF K_b and K_c of the longer and shorter branches are now evaluated along the obtained crack paths. Figure 2 plots the crack retardation factors (defined as the ratios between K_b or K_c and the Mode I SIF K_I of a straight crack) for $2\theta = 130^\circ$ and $m = 2$, as a function of the normalized length $(b-b_0)/b_0$ of the longer branch. Because of the different crack branch lengths, the SIF at the longer one is much higher than that at the shorter branch. Assuming K_b and K_c to be the crack driving force, it can be seen from Figure 2 that the longer branch reaches its minimum propagation rate right after the bifurcation occurs, returning to its pre-overload rate as the crack tip advances away from the influence of the shorter branch. As seen in the figure, the retardation behavior is misleadingly similar to closure-related effects, even though no closure is present in that case.

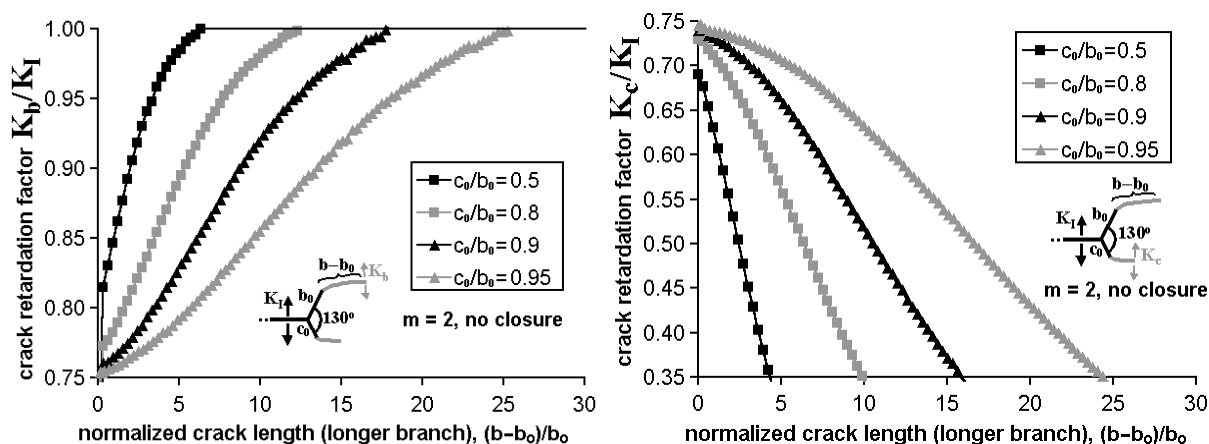


Fig. 2. Normalized equivalent SIF for the (a) longer and (b) shorter branch of a bifurcated crack during its propagation ($2\theta = 130^\circ$, $m = 2$, $K_{PR} = 0$).

An empirical expression is here proposed to model the SIF K_b of the longer branch during the transition between K_{b0} (the value of K_b immediately after the bifurcation event) and the straight-crack K_I (after the retardation effect ends), valid for $b_0 \leq b \leq b_f$ and $0.7 < c_0/b_0 < 1$:

$$K_b = K_{b0} + (K_I - K_{b0}) \cdot \left[\operatorname{atan}\left(3 \frac{b-b_0}{b_f-b_0}\right) / 1.25 \right]^{2c_0/b_0} \quad (5)$$

where b_f is given in Equation (4) and K_{b0} (and K_{c0}) by

$$\frac{K_{b0}}{K_I} = 0.75 + (1 - \sin \theta) \cdot \left(1 - \frac{c_0}{b_0}\right), \quad \frac{K_{c0}}{K_I} = 0.75 - (1 - \sin \theta) \cdot \left(1 - \frac{c_0}{b_0}\right) \quad (6)$$

It must be pointed out, however, that the presented FE results and empirical models might have some limitations, because actual bifurcations can be of a size comparable to the scale of the local plasticity (e.g., of the plastic zone size) or microstructural features (e.g., of the grain size). Moreover, possible environmental effects should be considered when comparing the bifurcation model predictions with measured crack growth rates (Suresh, 1983). However, one could argue that similar limitations would also apply to straight and in particular to curved crack propagation problems, since the crack increments (which are of the order of the CTOD, or of K^2/ES_Y , where E is Young's modulus and S_Y the yield strength) are at least two orders of magnitude smaller than the scale of the local plasticity (which is proportional to $(K/S_Y)^2$) in all these cases. But nevertheless 2D LEFM concepts are highly successful in modeling those problems when the local plasticity is much smaller than the cracked piece dimensions (Miranda et al., 2002; Miranda et al., 2003). In other words, experience has validated the use of a global SIF elastic parameter to predict the direction and the amount of the local crack increment, which is much smaller than the size of the plastic zones that always accompany the crack tip. Using these same concepts to describe the path and propagation life of a bifurcated crack under similar small scale yielding conditions (but not to describe how it bifurcates after an overload, e.g.) thus seems a very reasonable initial modeling approach for such problems (pending, of course, support by proper experimental verification). The interaction between crack branching and other retardation mechanisms is studied next.

4. BRANCHED CRACK PROPAGATION UNDER NEAR THRESHOLD CONDITIONS

All presented branched growth simulations so far have not included the effect of other retardation mechanisms, which can be significant especially under near-threshold conditions. This effect is easily accounted for in the FE calculations using Equation (3). The limiting value K_{PR} is assumed to be the same at both branch tips and always larger than the minimum SIF of each branch. Further simulations are then conducted considering several K_{PR} values, normalized by the maximum Mode I SIF K_I of the straight crack, namely $K_{PR}/K_I = \{0.067, 0.08, 0.10, 0.13, 0.20, 0.25, 0.40, 0.57\}$.

A generalized version of Equation (4) is then proposed to fit the calculated process zone sizes including the combined effects of other mechanisms:

$$\frac{b_f}{b_0} = \frac{\alpha}{(1 - c_0/b_0)^{(12-m)/20}} \cdot \exp\left[\frac{-\beta}{(1 - c_0/b_0)^\gamma} \cdot \frac{K_{PR}}{K_I}\right] \quad (7)$$

where

$$\alpha = \exp\left(\frac{2\theta - 30^\circ}{56 + 17 \cdot (m-2)^{2/3}}\right) \quad (8)$$

$$\beta = \left(\frac{2\theta}{110 + 60 \cdot (m-2)^{0.6}}\right)^{5/2} \quad (9)$$

$$\gamma = \frac{180^\circ - 2\theta}{280 - 130 \cdot (m-2)^{0.3}} \quad (10)$$

Figure 3 shows the effect of K_{PR} at the branch tips on the retardation factor for $2\theta = 130^\circ$, $c_0/b_0 = 0.9$ and $m = 2$. Note that higher K_{PR} levels reduce the size of the retardation process zone, due to premature arrest of the shorter branch. In Figure 3, e.g., the normalized size of the process zone is reduced from 18 to 3.6 as K_{PR}/K_I approaches 0.74, a factor of 5. In this example, 0.74 is the minimum K_{PR}/K_I level that prevents the shorter branch to even start propagating. Therefore, at any level above 0.74 the normalized process zone size will also be 3.6, because the propagation geometry will remain unchanged as long as the shorter branch remains arrested at $c = c_0$.

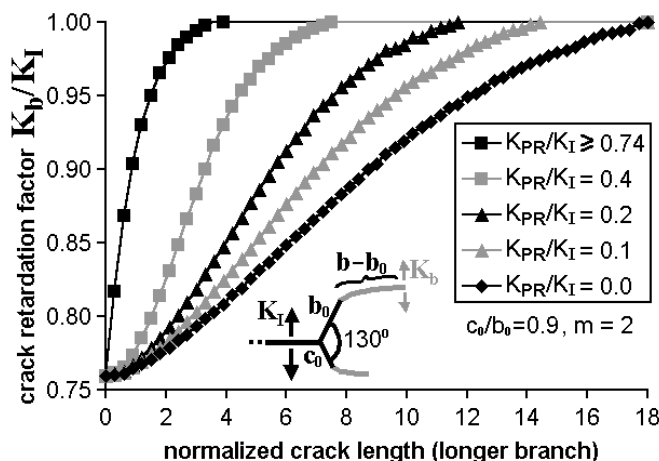


Fig. 3. Normalized SIF of the longer branch during its propagation as a function of the normalized length $(b-b_0)/b_0$ for several K_{PR} levels ($c_0/b_0 = 0.9$, $m = 2$).

Note, however, that a smaller process zone does not necessarily mean fewer delay cycles, since the longer branch will also experience a reduction in the crack propagation rate due to other retardation mechanisms. Therefore, a competition between lower growth rates of the longer branch and smaller bifurcation process zone sizes will take place to determine the real effect of combining bifurcation with other retardation mechanisms.

Equations (7-10) and (6) can then be applied to Equation (5) to model the SIF K_b of the longer branch during the transition between K_{b0} (the SIF immediately after the bifurcation event) and the straight-crack K_I (the SIF after the end of the retardation effect), completing this analysis.

5. EXPERIMENTAL RESULTS

Quantitative validations of the predicted bifurcated crack growth behavior are performed on Eccentrically-loaded Single Edge Crack Tension specimens ESE(T) made from an annealed SAE 4340 low-alloy steel with $S_Y = 377\text{MPa}$, $S_U = 660\text{MPa}$, $E = 205\text{GPa}$, and $RA = 52.7\%$, and with the analyzed weight percent composition: C 0.37, Mn 0.56, Si 0.14, Ni 1.53, Cr 0.64, Mo 0.18, S 0.04, P 0.035. The tests are performed at frequencies between 20 and 30Hz in a 250kN computer-controlled servo-hydraulic testing machine. The crack length is measured following ASTM E 647 procedures (ASTM Standard E 647). Special attention is given for crack closure measurements, made using a high speed data acquisition system to obtain data and to avoid intervention during the tests. In this way, the load and Crack-Opening Displacement (COD) data are used to precisely compute the crack closure load using a digital implementation of the linearity subtractor circuit developed to enhance the opening load, (Paris and Hermann, 1976) (the accuracy of such careful closure load measurements is in the order of $K_{max}/100$ (Castro, 1993)).

The proposed retardation equations are implemented in a fatigue life assessment program named ViDa (Miranda et al., 2002; Miranda et al., 2003). This program is used to estimate the number of delay cycles associated with the experimentally obtained bifurcation on the 4340 steel ESE(T) specimen. The number of cycles spent during the propagation in the retardation region is then calculated by integrating the da/dN equation along the longer crack branch, from $b = b_0$ to $b = b_f$.

Four tests are performed on ESE(T) specimens subject to 100% overloads, namely tests I, II, III and IV: (I) $R = 0.7$, $\Delta K = 13.9\text{MPa}\sqrt{\text{m}}$, resulting in approximately 22,000 delay cycles; (II) $R = 0.7$, $\Delta K = 14.2\text{MPa}\sqrt{\text{m}}$, resulting in approximately 20,000 delay cycles; (III) $R = 0.7$, $\Delta K = 13.7\text{MPa}\sqrt{\text{m}}$, resulting in approximately 27,000 delay cycles; (IV) $R = 0.05$, $\Delta K = 16.2\text{MPa}\sqrt{\text{m}}$, resulting in approximately 32,000 delay cycles, see Figs. 4-11.

It is found that the minimum load levels in tests I and II are always above the opening load, therefore no crack closure is present nor before nor after the overloads. For test I, the measured initial branch lengths are approximately $b_0 = 9\mu\text{m}$ and $c_0 = 8.5\mu\text{m}$, with a bifurcation angle $2\theta = 160^\circ$, see Fig. 9(a). The material is modeled using Equation (1) with crack growth constants $A = 9 \cdot 10^{-11}\text{m/cycle}$ and $m = 2.1$, and a propagation threshold $\Delta K_{th} = 2.8\text{MPa}\sqrt{\text{m}}$, measured under $R = 0.7$. From Equation (6), it is found that $K_{b_0}/K_I = 0.751$ and $K_{c_0}/K_I = 0.749$, leading to $\Delta K_{b_0} = 0.751 \cdot \Delta K_I = 10.437\text{MPa}\sqrt{\text{m}}$ and $\Delta K_{c_0} = 0.749 \cdot \Delta K_I = 10.413\text{MPa}\sqrt{\text{m}}$. Since both ranges are greater than $\Delta K_{th}(R=0.7) = 2.8\text{MPa}\sqrt{\text{m}}$, both branches are expected to start propagating, as verified experimentally. The size of the process zone can be estimated from Equation (4), which results in $b_f = 36.95 \times 9\mu\text{m} \cong 332\mu\text{m}$. The number of delay cycles is then calculated by integration, $n_D = 9,664$ cycles, which is approximately half of the measured 22,000 delay cycles (Fig. 5(a)).

For test II, the measured initial branch lengths are approximately $b_0 = 10\mu\text{m}$ and $c_0 = 9.5\mu\text{m}$, but with a larger bifurcation angle $2\theta = 160^\circ$, see Fig. 9(b), resulting in 10,669 cycles, which is also about half of the measured 20,000 delay cycles (Fig. 5(b)).

Figure 6(a) shows a crack retardation of approximately 27,000 delay cycles resulting from test III. However, in this case the external polished surfaces of the specimen did not present any signs of bifurcation. But careful inspection of the fracture surfaces using a scanning electron microscope revealed that not only tests I and II but also test III resulted in a bifurcation front along the specimen thickness, see Figs. 7-9. The bifurcation front is approximately straight and through-the-thickness for tests I and II, but surprisingly for test III the front is discontinuous towards the specimen faces, indicating an internal bifurcation. Despite its 3-D geometry, the retardation behavior is still reasonably reproduced by the proposed 2-D model within a factor of 2 in number of delay cycles.

For test IV, the initial branch lengths are approximately $b_0 = 10\mu\text{m}$ and $c_0 = 9.5\mu\text{m}$, with a bifurcation angle $2\theta = 150^\circ$, see Fig. 10. The material is modeled using Equation (1) with crack growth constants $A = 9 \cdot 10^{-11}\text{m/cycle}$ and $m = 2.2$, and a propagation threshold $\Delta K_{th} = 8.1\text{MPa}\sqrt{\text{m}}$, all measured under $R = 0.05$. The size of the process zone is calculated from Equations (7-10), resulting in $\alpha = 6.97$, $\beta = 1.35$, $\gamma = 0.15$, and $b_f = 11.6 \times 10\mu\text{m} \cong 116\mu\text{m}$. Using the same process described previously, the delay cycles $n_D = 17,316$ cycles, which is about half of the measured 32,000 delay cycles, see Fig. 6(b).

Note that in all tests there was no retardation induced by crack closure. The only test in which crack closure was detected was test IV, however after the overload the opening load in fact decreased, see Fig. 11. The opening load remained lower than before the overload along the entire process zone, only returning to its original value after the bifurcation effect had ended. Therefore, even if closure affected the constant amplitude growth behavior in test IV, it would not be able to explain the measured overload-induced retardation. This behavior has already been described in the literature (Meggiolaro and Castro, 2003).

The errors in the predictions performed using the proposed semi-empirical equations can be explained by inaccuracies in the estimation of the initial branch lengths b_0 and c_0 , since the retardation effect is highly dependent on the ratio c_0/b_0 . In addition, other retardation mechanisms besides bifurcation (except for closure, as discussed above) might be contributing to increase the number of delay cycles, such as unmodeled unaccounted? environmental effects or further kinking of the branch tips due to microstructure inhomogeneities. Another factor could be a specimen thickness effect, where the plane strain condition assumed in the 2-D calculations would result in less retardation than the actual 3-D stress state. However, the retardation mechanism behind a possible thickness effect in the performed experiments could

not be crack closure, as shown in Fig. 11. Small differences between the actual crack growth behavior and the assumed crack propagation rule (particularly in the curvature of the transition from the threshold or phase I to the Paris or phase II regions) can also be a cause for these prediction inaccuracies. In any case, the presented predictions are of the same order of magnitude of the experimental scatter. Therefore, the quantitative approach presented in this work is a quite promising tool for modeling and calculating overload-induced retardation effects where other mechanisms have failed to give a satisfactory explanation.

Finally, it must be noted as well that all measured bifurcations occurred throughout the thickness in an approximately uniform pattern (except near the specimen faces for test III), observed after carefully slicing and reexamining the specimens. Therefore, despite the inherent 3-D nature of the bifurcation problem, in these tests the presented two-dimensional FE approach has been validated.

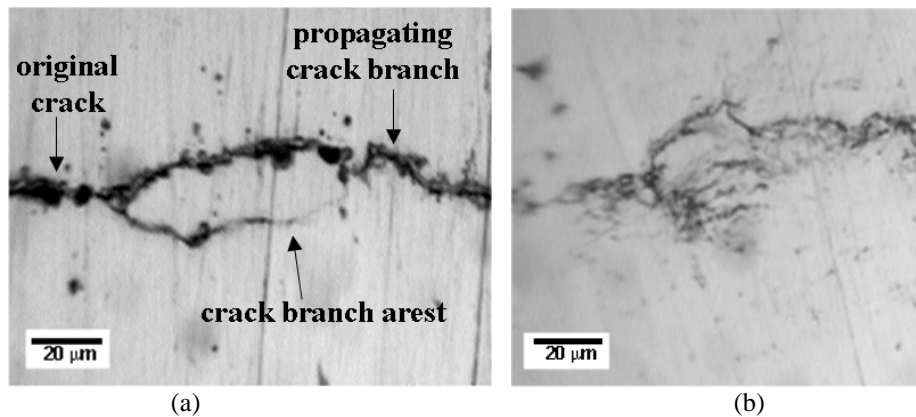


Fig. 4. Crack bifurcation experiments on SAE 4340 steel: (a) test I, (b) test II.

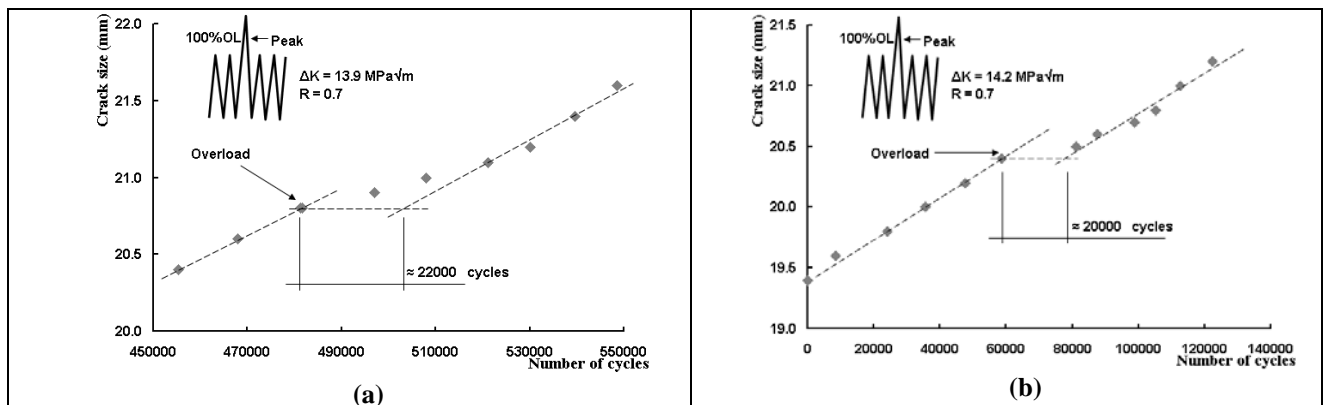


Fig. 5. Fatigue crack growth retardation after a 100% overload with $R = 0.7$: (a) test I and (b) test II.

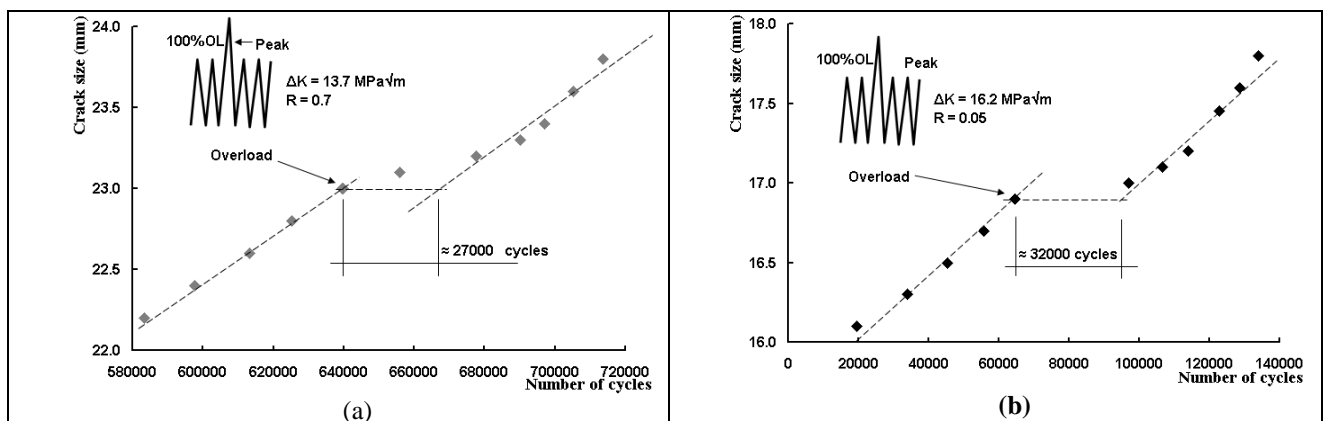


Fig. 6. Fatigue crack growth retardation after a 100 % overload: (a) $R = 0.7$, test III; (b) $R = 0.05$, test IV.

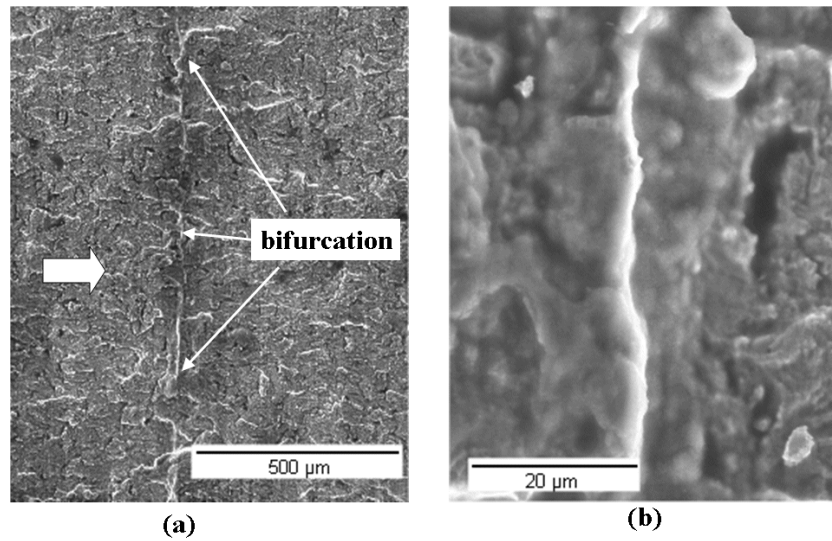


Fig. 7. Scanning electron micrographs of fracture surfaces (test I): (a) bifurcation front through the specimen thickness, and (b) detailed view indicating different height levels.

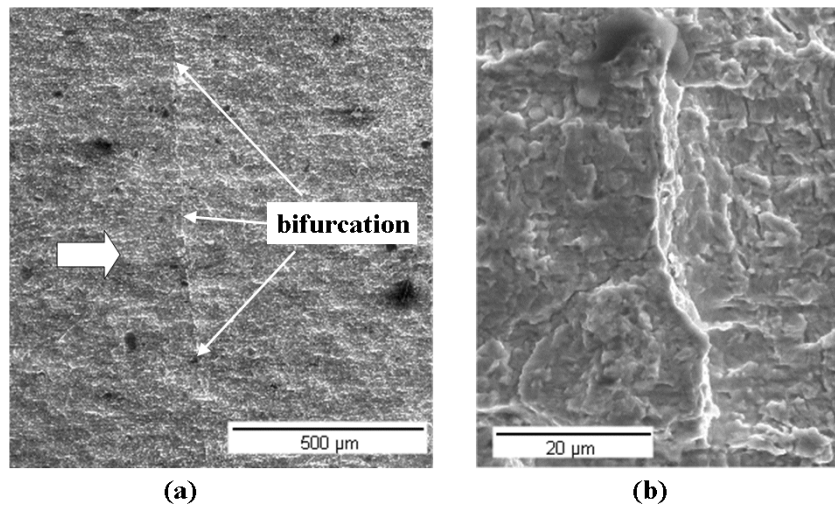


Fig. 8. Scanning electron micrographs of fracture surfaces (test II): (a) bifurcation front through the specimen thickness, and (b) detailed view indicating different height levels.

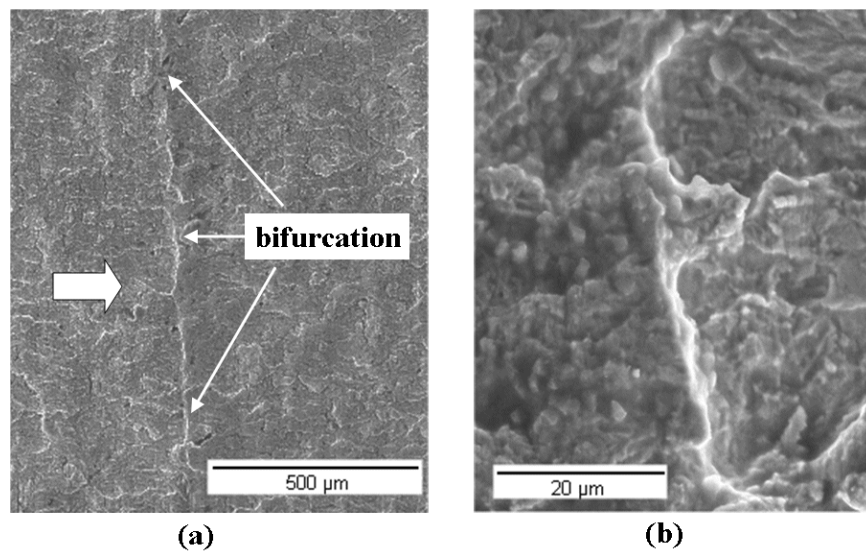


Fig. 9. Scanning electron micrographs of fracture surfaces (test III): (a) bifurcation front through the specimen thickness, and (b) detailed view indicating different height levels.

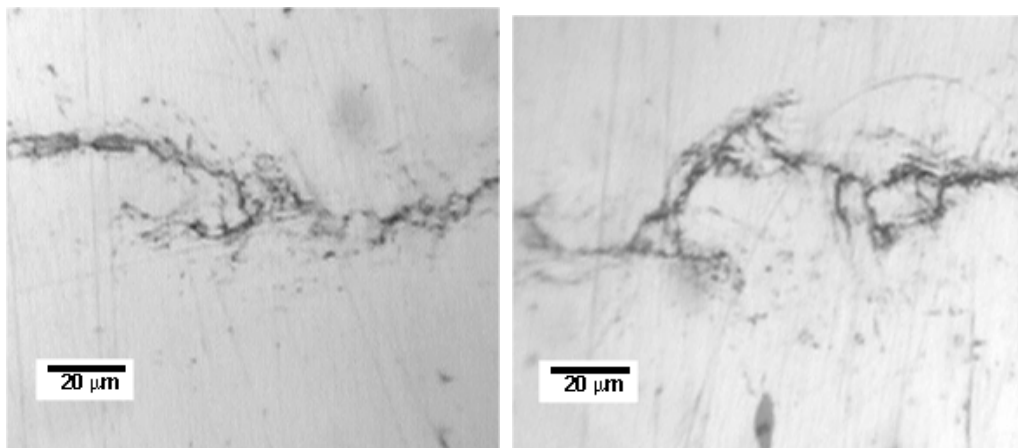


Fig. 10. Crack bifurcation experiments on SAE 4340 steel (test IV): (a) front face of specimen (b) back face of specimen.

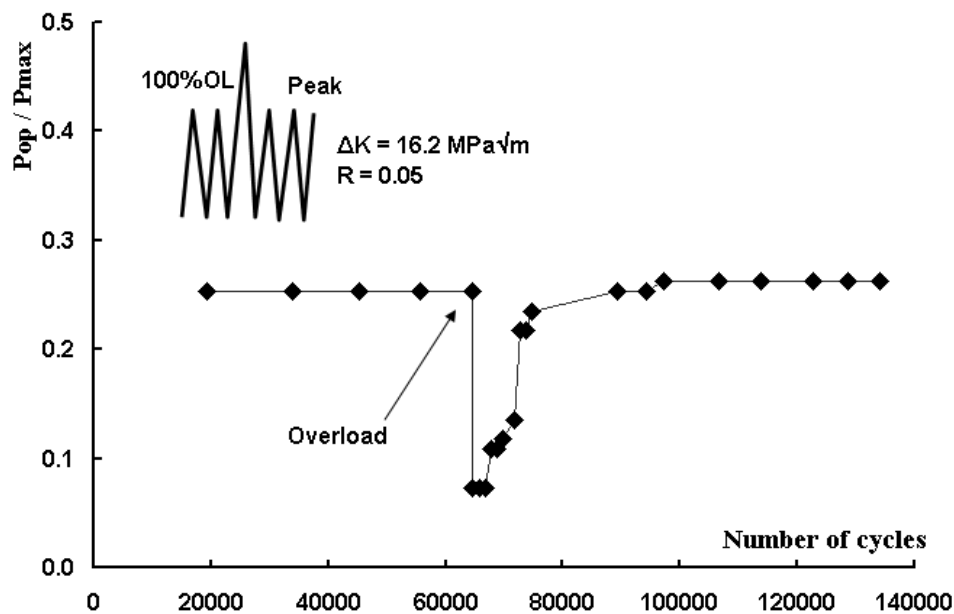


Fig. 11. Opening load measurements, before and after the overload (test IV).

6. CONCLUSIONS

In this work, a specialized FE program was used to calculate the propagation path and associated stress intensity factors (SIF) of bifurcated cracks, which can cause crack retardation or even arrest. In particular, the bifurcation simulations included several combinations of bifurcation angles $2\theta = \{40^\circ, 80^\circ, 90^\circ, 130^\circ, 168^\circ\}$, branch asymmetry ratios $c_0/b_0 = \{0.5, 0.7, 0.8, 0.9, 0.95, 1.0\}$, crack growth exponents $m = \{2, 3, 4\}$, and even considered interaction between crack branching and other retardation mechanisms through the threshold ratios $K_{PR}/K_I = \{0.0, 0.067, 0.08, 0.10, 0.13, 0.20, 0.25, 0.40, 0.57\}$. The proposed equations, besides capturing all above described phenomena, can be readily used to predict the propagation behavior of branched and kinked cracks in an arbitrary structure, as long as the process zone ahead of the crack tip is small compared to the other characteristic dimensions, exactly as in other similar fatigue propagation problems such as curved crack path and life predictions. However, these predictions probably should also be limited to the cases where it can be assumed that the entire crack-front bifurcates uniformly (as observed by scanning electron microscopy in the tests reported in this work), where the specimen thickness itself may provide the size scale requirements for the validity of the presented 2D LEFM-based equations, as the calculated SIF may be averaged considering the (several) grains present along the thickness. Otherwise, if the crack deflections vary significantly along the thickness, then 3D modeling including Mode III effects should be considered. From these results, it can be seen that crack bifurcation may provide an alternate mechanistic explanation for overload-induced crack retardation on structural components, especially to explain load interaction effects under closure-free conditions.

7. ACKNOWLEDGMENTS

CNPq has provided research scholarships for Castro, JTP and Meggiolaro, MA.

8. REFERENCES

- ASTM Standard E 647. *Standard Test Method for Measurement of Fatigue Crack Growth Rates*. ASTM Standards;03.01
- Castro JTP. *A Circuit to Measure Crack Closure*. Exp. Techniques 1993;17(2):23-25.
- Erdogan, F., Sih, G.C. *On the Crack Extension in Plates under Plane Loading and Transverse Shear*. Journal of Basic Engineering. 1963;85:519-527.
- Karihaloo BL. *On Crack Kinking and Curving*. Mechanics of Materials 1982;1:189-201.
- Lang M, Marci G. *The influence of single and multiple overloads on fatigue crack propagation*. Fatigue and Fracture of Engineering Materials and Structures 1999;22:257-271.
- Lankford J, Davidson DL. *The Effect of Overloads upon Fatigue Crack Tip Opening Displacement and Crack Tip Opening/Closing Loads in Aluminum Alloys*. Advances In Fracture Research, Pergamon Press 1981;2:899-906.
- Meggiolaro MA, Castro JTP. *On the dominant role of crack closure on fatigue crack growth modeling*. International Journal of Fatigue 2003;25(9-11):843-854.
- Miranda ACO, Meggiolaro MA, Castro JTP, Martha LF, Bittencourt TN. *Fatigue Crack Propagation under Complex Loading in Arbitrary 2D Geometries*. ASTM STP 1411, 2002;4:120-46.
- Miranda ACO, Meggiolaro MA, Castro JTP, Martha LF, Bittencourt TN. *Fatigue Life and Crack Path Prediction in Generic 2D Structural Components*. Eng. Fracture Mechanics 2003;70:1259-79.
- Paris P, Hermann L, *Int. Cong. App. Mech.*, Delft, 1976
- Pärletun LG. *Determination of the growth of branched cracks by numerical methods*. Engineering Fracture Mechanics 1979;11:343-358
- Sadananda K, Vasudevan AK, Holtz RL. *Extension of the Unified Approach to Fatigue Crack Growth to Environmental Interactions*. International Journal of Fatigue 2001;23:S277-S286.
- Suresh S. *Crack Deflection: Implications for the Growth of Long and Short Fatigue Cracks*. Metallurgical Transactions 1983;14a:2375-85.

9. RESPONSIBILITY NOTICE

The author(s) is (are) the only responsible for the printed material included in this paper.